













RESEARCH

Open Access



# The glycocalyx affects the mechanotransductive perception of the topographical microenvironment

Matteo Chighizola<sup>1†</sup>, Tania Dini<sup>1,2</sup>, Stefania Marcotti<sup>3</sup>, Mirko D'Urso<sup>1,4</sup>, Claudio Piazzoni<sup>1</sup>,  
Francesca Borghi<sup>1</sup>, Anita Previdi<sup>1</sup>, Laura Ceriani<sup>1</sup>, Claudia Folliero<sup>1,2</sup>, Brian Stramer<sup>3</sup>, Cristina Lenardi<sup>1</sup>,  
Paolo Milani<sup>1</sup>, Alessandro Podestà<sup>1\*†</sup> and Carsten Schulte<sup>1\*†</sup>

## Abstract

The cell/microenvironment interface is the starting point of integrin-mediated mechanotransduction, but many details of mechanotransductive signal integration remain elusive due to the complexity of the involved (extra)cellular structures, such as the glycocalyx. We used nano-bio-interfaces reproducing the complex nanotopographical features of the extracellular matrix to analyse the glycocalyx impact on PC12 cell mechanosensing at the nanoscale (*e.g.*, by force spectroscopy with functionalised probes). Our data demonstrates that the glycocalyx configuration affects spatio-temporal nanotopography-sensitive mechanotransductive events at the cell/microenvironment interface. Opposing effects of major glycocalyx removal were observed, when comparing flat and specific nanotopographical conditions. The excessive retrograde actin flow speed and force loading are strongly reduced on certain nanotopographies upon strong reduction of the native glycocalyx, while on the flat substrate we observe the opposite trend. Our results highlight the importance of the glycocalyx configuration in a molecular clutch force loading-dependent cellular mechanism for mechanosensing of microenvironmental nanotopographical features.

**Keywords:** Mechanotransduction, Glycocalyx, Integrin adhesion complexes, Molecular clutch, Force loading, Focal adhesion, Nanostructured cell microenvironment, Nanotopography, Adhesion force spectroscopy, Atomic force microscopy, Colloidal probes

<sup>†</sup>Matteo Chighizola is first author to this work

<sup>†</sup>Carsten Schulte and Alessandro Podestà Co-last authors to this work


\*Correspondence: [alessandro.podesta@mi.infn.it](mailto:alessandro.podesta@mi.infn.it); [carsten.schulte@unimi.it](mailto:carsten.schulte@unimi.it)

<sup>1</sup> Interdisciplinary Centre for Nanostructured Materials and Interfaces (C.I.Ma.I.Na.) and Department of Physics "Aldo Pontremoli", University of Milan, Milan, Italy

Full list of author information is available at the end of the article



© The Author(s) 2022. **Open Access** This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons licence, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons licence, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons licence and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this licence, visit <http://creativecommons.org/licenses/by/4.0/>. The Creative Commons Public Domain Dedication waiver (<http://creativecommons.org/publicdomain/zero/1.0/>) applies to the data made available in this article, unless otherwise stated in a credit line to the data.

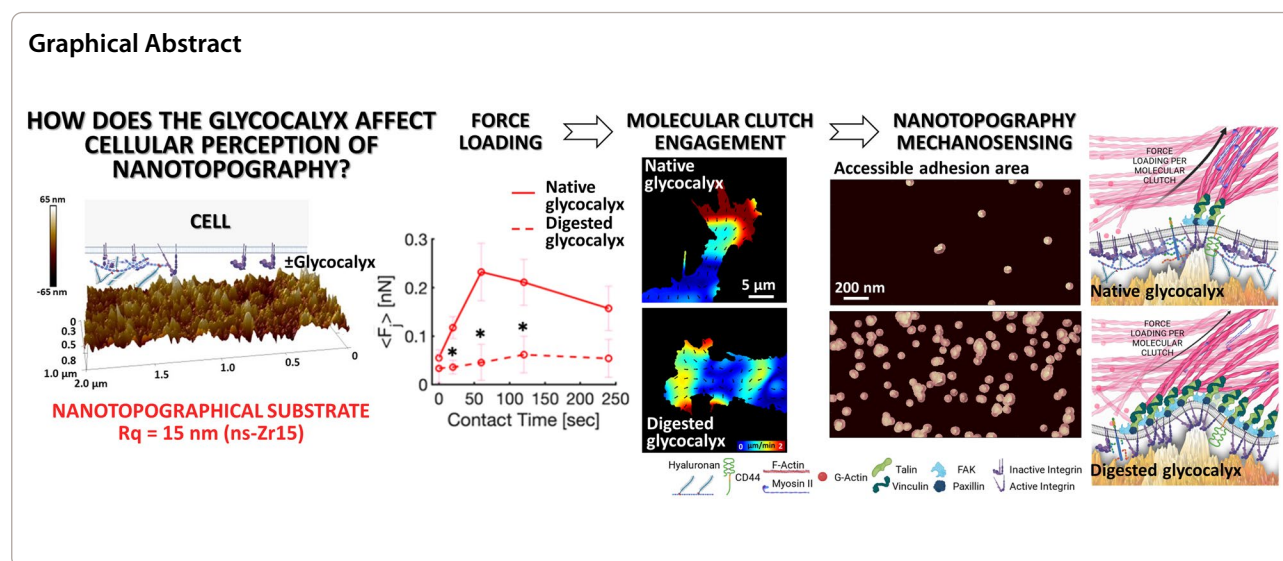

## Introduction


In recent years, there has been accumulating evidence of the pivotal importance of integrin-mediated mechanosensing and mechanotransduction, i.e., the conversion of biophysical cues from the microenvironment into cellular responses. The events at the interface between the cell and the extracellular matrix (ECM) are at the base of mechanotransductive processes. At this interface, the microenvironmental biophysical cues are translated into intracellular signals, with integrin adhesion complexes (IAC) as the major relay stations. Linkages between the ECM and the actin filaments (f-actin) via integrin and talin, i.e., the formation of so-called molecular clutches, enable force transmission from the retrograde actin flow, which, in turn, is generated by actin polymerisation and the myosin-driven contraction of f-actin. These interfacial actions depend on the structural and biophysical ECM properties and regulate in an intricate manner the force loading within the molecular clutches, the maturation of IAC into signalling platforms, and cytoskeletal remodelling, which together convert into cellular responses [1–6]. The involved (extra)cellular structures in this cell/microenvironment interface, such as the ECM, the glycocalyx, the cell membrane, the IAC and the cytoskeleton, are highly complex and their sophisticated crosstalk is only partially understood.

The ECM nanotopography represents an important biophysical cue for mechanotransductive processes. The configuration of the topographical nano- three-dimensional (3D) features of the ECM sets the spatial parameters relevant for mechanosensing, such as adhesion site areas and spacing, and is therefore capable of modulating IAC formation and signalling [6–13]. Intrinsic cellular parameters can furthermore influence the cell interface

with the nanotopography. The cellular cortical stiffness affects the extent to which the cell membrane can deform and contact the intervening nanostructured surface which, in turn, defines the effective accessible cell/substrate contact area at the nanoscale [14, 15]. Our previous work demonstrated that the availability of activated integrins also regulates nanotopography mechanosensing and force loading [16].

An underappreciated player in mechanotransduction is the glycocalyx, a pericellular sugar coat that is attached to the cell surface and involved in cellular adhesive processes. It is known that the glycocalyx can promote integrin clustering and influence membrane bending [2, 17–25]. However, the studies in this context have been done on flat substrates and therefore many details about the impact of the glycocalyx on the nanotopography-dependent processes at the cell-microenvironment interface, such as force loading in molecular clutches, remain elusive; which is one of the main rationales behind this work. To this end, we studied how the glycocalyx affects the cellular capability to perceive and react to the nanotopography and impacts molecular clutch engagement and force loading (Fig. 1).

Our approach consists in measuring the integrin-related interaction forces between living cells and suitable probes or substrates, functionalised by gas-phase assembling of biocompatible zirconia nanoparticle [26, 27]. These nano-bio interfaces are characterised by a disordered surface topography and a random distribution of asperities and valleys, whose dimensions and relative distances resemble the ECM organisation at the micro/nanoscale [16, 28, 29] (Fig. 1A). The potential of these topographies to modulate mechanotransductive

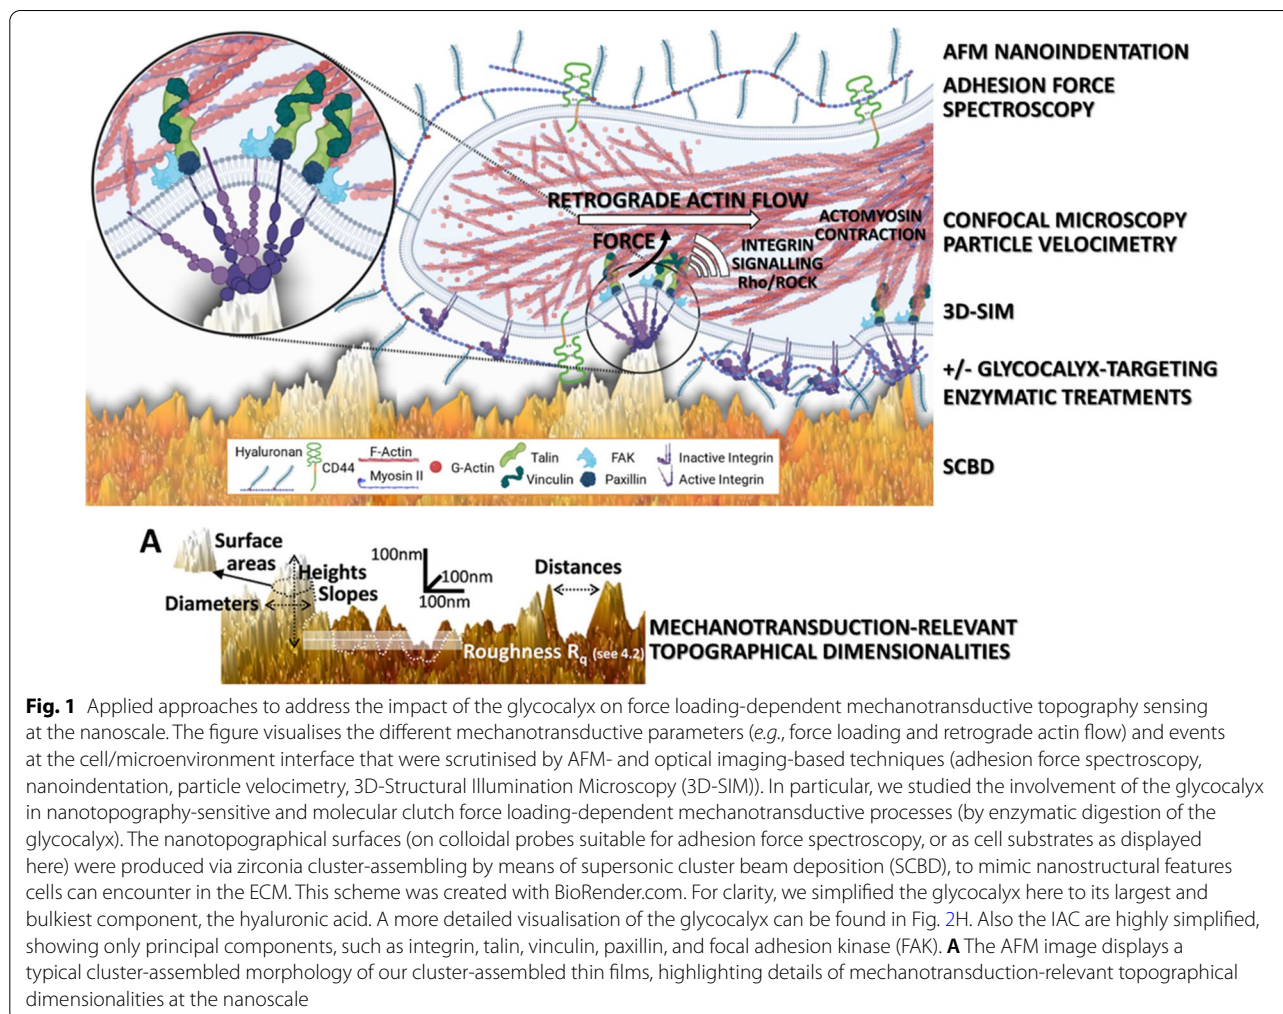

processes [9, 10, 13, 27], as well as cellular functioning, programme and differentiation in various cell biological contexts [9, 13, 30–33], has already been documented.

Here, we aimed to dissect the role of the glycocalyx in spatio-temporal events that occur at the early stages of cell/microenvironment interaction (during IAC formation) and during nanotopography mechanosensing at long-term interaction in lamellipodia. We modelled the contact interaction geometry of cells with different nanotopographical features, as a function of cell membrane compliance with the surface, to obtain insight in the cues perceived by the cell. To analyse the early dynamics of mechanotransductive events by AFM-based adhesion force spectroscopy approaches, we challenged PC12 cells with different nanotopographical probes and manipulated the glycocalyx and the ROCK-dependent actomyosin contractility. The neuronal-like PC12 cell model was selected due to our previous studies that demonstrated how nanotopographical features robustly modulate the mechanotransductive structures and signalling in these


cells [9, 10, 16]. We furthermore studied, by means of optical imaging techniques, the impact of the nanotopography and glycocalyx on molecular clutch engagement to the retrograde actin flow in lamellipodia.

## Results and discussion

### Structural assessment of the native PC12 cell glycocalyx


We first investigated the structural configuration of the native glycocalyx of PC12 cells, by AFM- and 3D-SIM-based techniques (Fig. 2) and assessed the efficiency of a comprehensive glycocalyx-targeting enzymatic treatment, consisting of a cocktail of hyaluronidase II, chondroitinase ABC, heparinase III, and neuraminidase, in removing the glycocalyx.

We performed AFM indentation experiments to test the mechanical and structural properties of the glycocalyx of live PC12 cells, based on the protocol developed by Sokolov et al. [34–37] (Fig. 2 A–D). The rescaled force curves from the untreated cells show a bilinear regime in the semi-logarithmic scale (Fig. 2A,B). This behaviour is

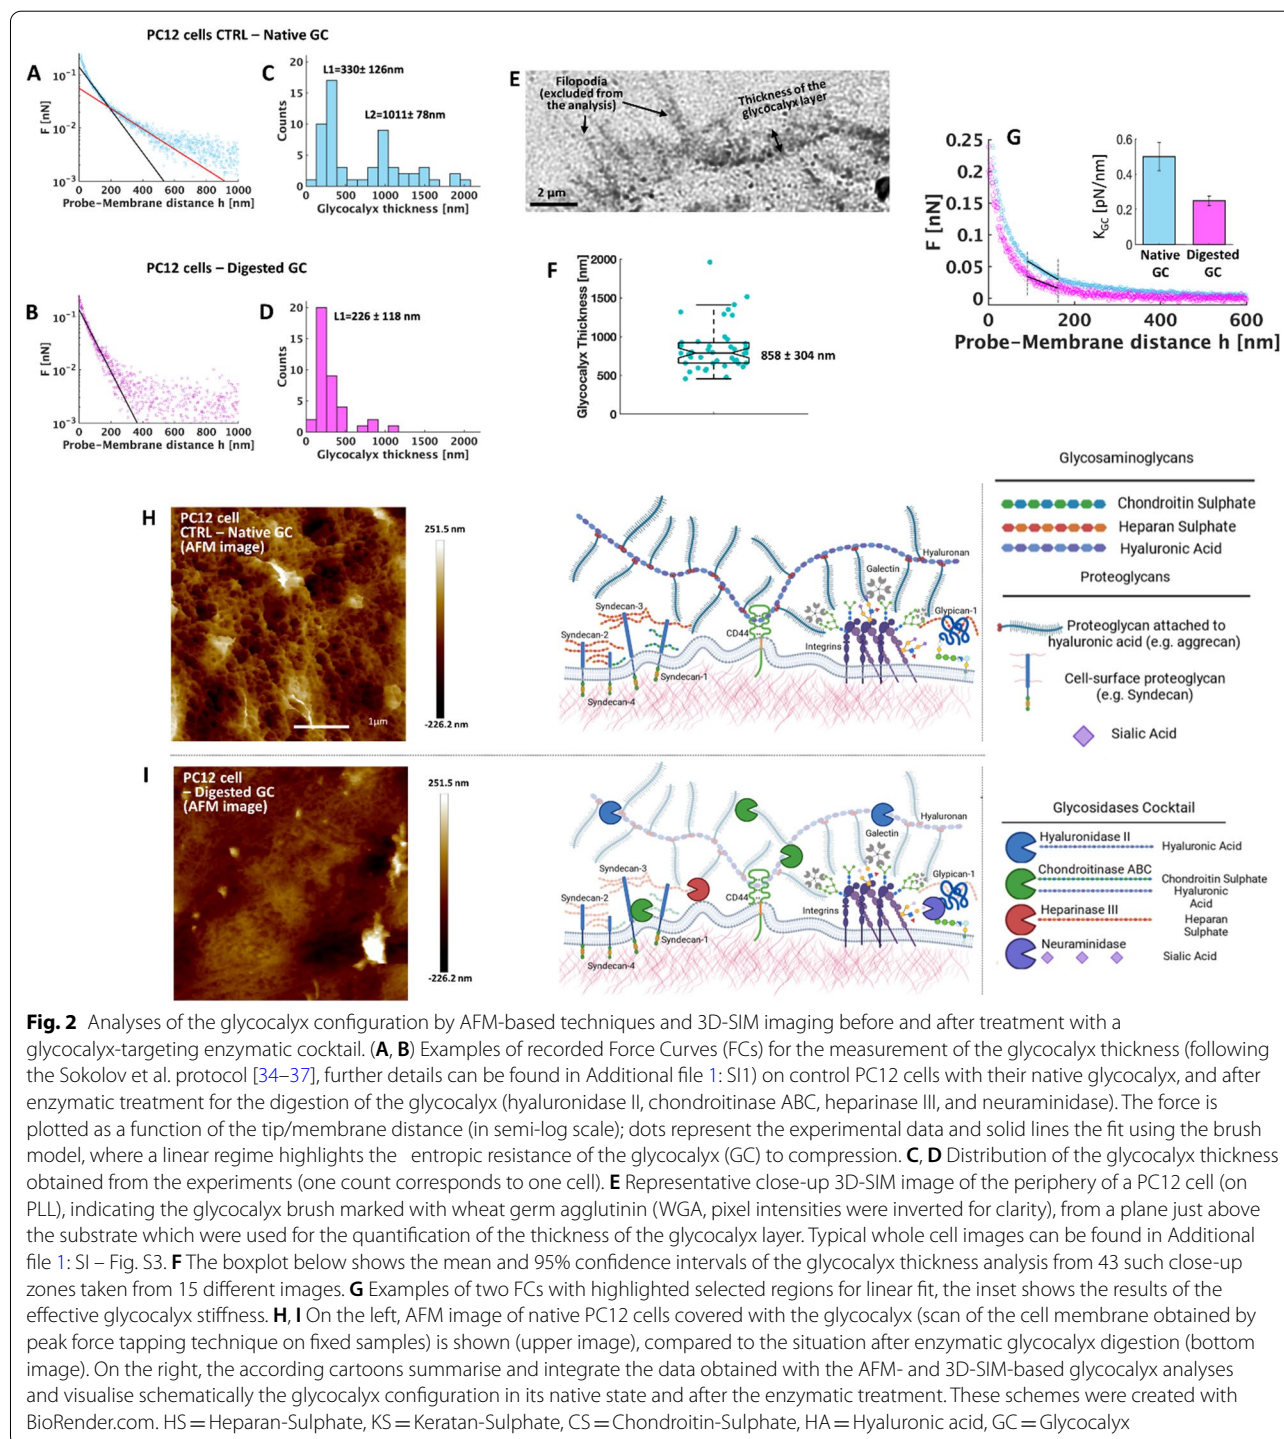

commonly associated with the presence of two glycocalyx components [35], one longer (red line in Fig. 2A), and one shorter (black line in Fig. 2A,B). Conversely, for the cells treated with the enzymatic cocktail, the long component was mostly (90%) removed and only the short component was present (Fig. 2B).

The quantification of the control PC12 cells (Fig. 2C) demonstrated that the long and short components of the native glycocalyx have a thickness of  $1011 \pm 78$  nm and  $330 \pm 126$  nm, respectively (details on the Sokolov bilayer brush model and the long and short component can be

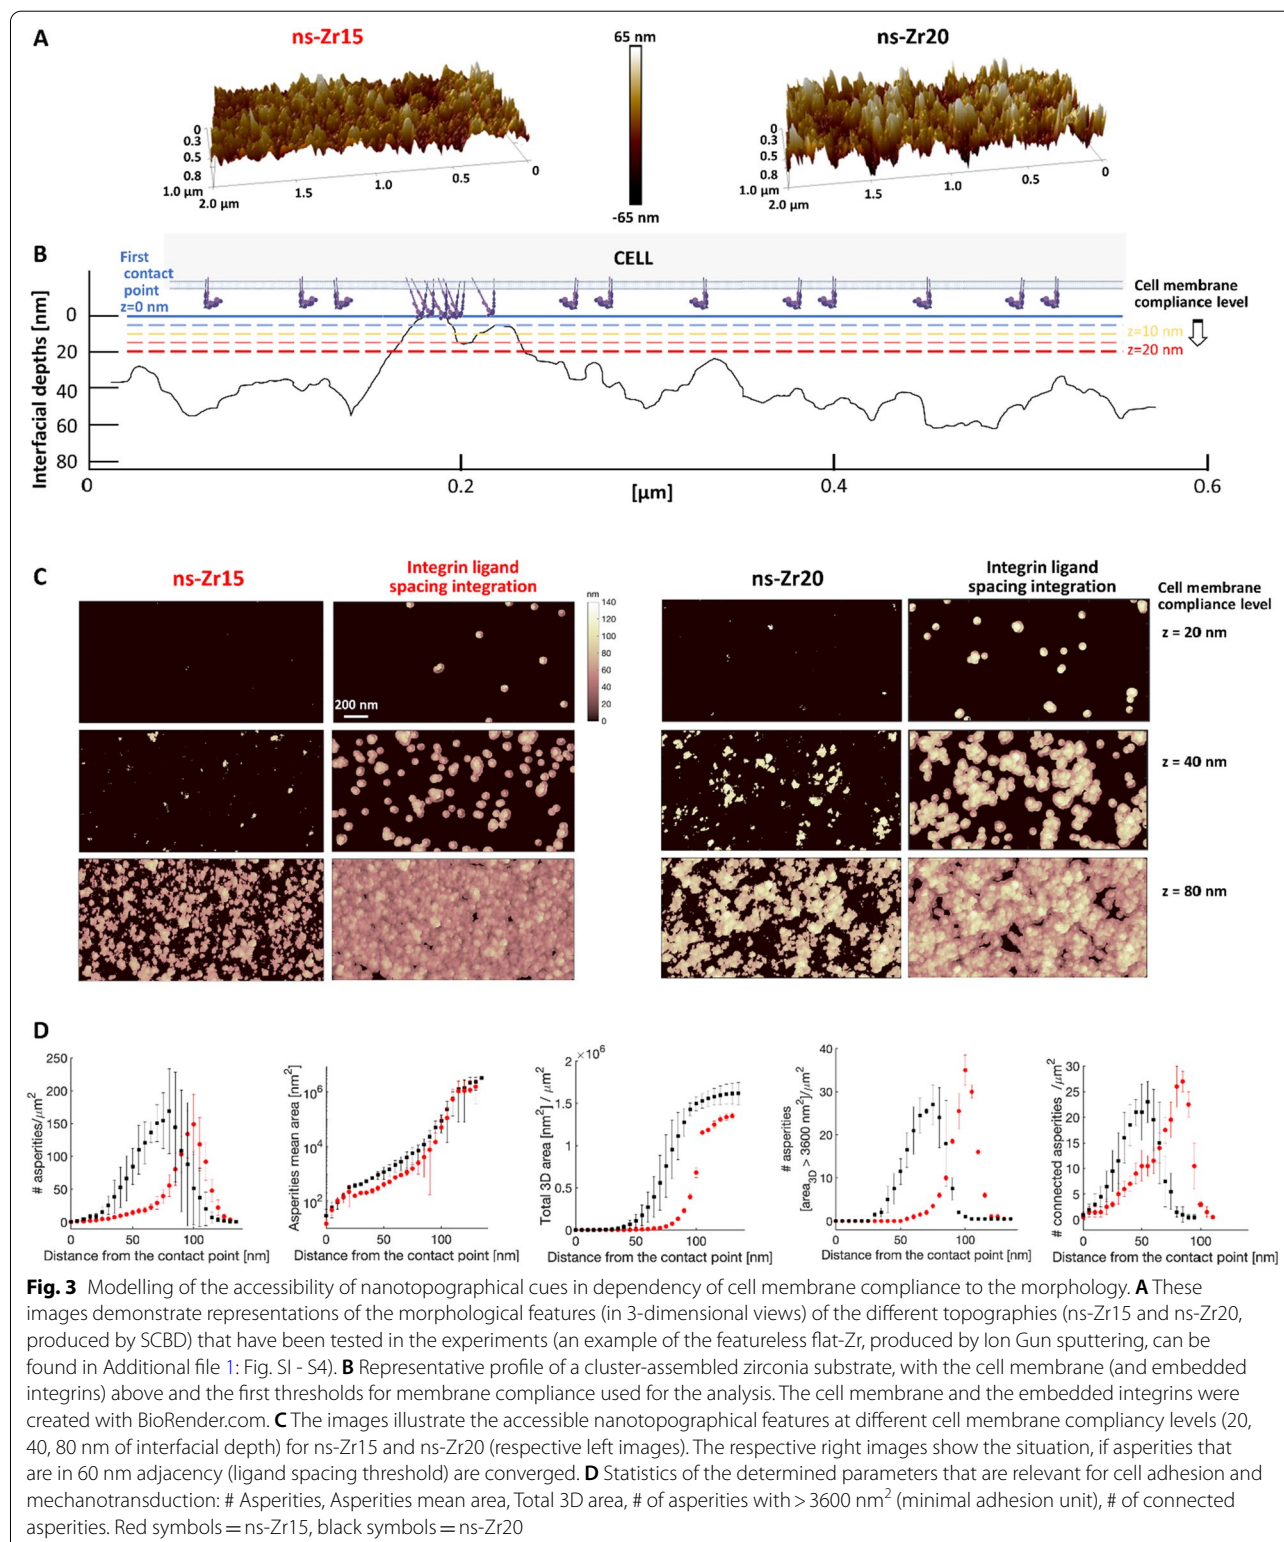

found in (Additional file 1: SI-Fig. S1-2)). The enzymatic digestion of the glycocalyx almost completely removed the long component of the glycosidic brush (Fig. 2D).

Only in 10% of the measured cells this long component was still present after the enzymatic treatment, and also it was significantly shorter (-21.4%) with a thickness of

795 ± 150 nm. The short component was still present, but also shortened by 31.5% to a thickness of 226 ± 118 nm (Fig. 2B,D).

3D-SIM super-resolution imaging of live PC12 cells (Fig. 2E, Additional file 1: SI-Fig. S3A,B) revealed the presence of abundant intracellular vesicles (through which glycolyx components are transported to the surface) and a clear pericellular sugar brush around the cells. We also detected migration tracks, extracellular structures/organelles left behind by many migrating cells [38–40] (Additional file 1: SI-Fig. S3A). The staining of the pericellular sugar coat and the migration tracks disappeared after enzymatic treatment, with only the intracellular vesicles remaining (Additional file 1: SI-Fig. S3B). Quantification of the thickness of this sugar coat at the border of the lamellipodial zones of the control cells revealed that it is 858.1 ± 304.3 nm thick, in good agreement with the values obtained by the AFM-based analysis (Fig. 2F).

The mechanical properties of the glycolyx have been tested following the so-called “mechanical spring model” approach (for details, see Methods “[Glycolyx characterisation by AFM nanoindentation](#)”). The results of the analyses demonstrate a glycolyx stiffness of  $K_{GC} = 0.50 \pm 0.08$  pN/nm that decreased ~50% after the enzyme digestion to  $K_{GC} = 0.24 \pm 0.03$  pN/nm (Fig. 2G).

Imaging of fixed PC12 cells (with or without enzymatic treatment) by AFM showed that the native cell surface was characterised by porous, reticular and filamentous structures (Fig. 2H), which became smooth after the enzymatic treatment with few remaining agglomerates (Fig. 2I).

Altogether, these findings confirmed the presence of a substantial glycolyx layer, approximately 1 µm thick, around native PC12 cells. Also, the efficacy of the enzymatic treatment was validated, leading to a major reduction of the glycolyx. It was, however, not complete and mostly attributable to the long component.

#### Modelling of the surface accessibility as a function of cell membrane compliance to the nanotopographies

In this work, we used three different topographies (typical representations of the morphological features are shown in Fig. 3A and Additional file 1: SI – Fig. S4-5): a featureless flat zirconia substrate (flat-Zr, produced by ion gun sputtering) with a roughness parameter  $R_q < 1$  nm, and two nanostructured zirconia substrates with a  $R_q = 15$  nm (ns-Zr15) and  $R_q = 20$  nm (ns-Zr20); the latter two produced by SCBD (fabrication details in 4.1–2). The structure and morphology of the nanostructured films result from the random stacking and aggregation of impinging nanometric particles of  $ZrO_2$  and closely mimic nanotopographical features that cells

encounter in ECM with spatial parameters that are relevant for mechanotransduction [16, 28, 29].

Compared to flat substrates, the three-dimensionality of the nanotopographical surfaces adds a critical level of morphological complexity to cell adhesion processes (Fig. 1A). The effective cellular contact area with a given nanotopography can vary decisively as corollary of the capability of the cell membrane and its embedded adhesion receptors to access, or not, the bottom parts of nanotopographical asperities. This is still a rather underestimated aspect, even though it was recently found by Park et al. [14, 15] that different compliance of the cell membrane with a nanotopography can impact important (patho)physiological cellular processes, such as cell migration and behaviour of metastatic cells. Our previous characterisations demonstrated that the dimensionalities of the nanotopographical asperities produced by SCBD influence mechanotransductive processes [9].

Moreover, work by Paszek et al. [18, 41] has shown that the glycolyx, as structure in the cell/microenvironment interface, forms a steric barrier for integrin/ligand binding outside of already established adhesion sites with the substrate, due to its bulkiness and compression [1, 2], and can impact the membrane bending [23]. However, these studies were performed in the context of flat substrates. It can be hypothesised that, also in the case of nanotopographical substrates, the presence of a long glycolyx (e.g., hundreds of nm for the PC12 cells, Fig. 2C,E,F,H) will impede the access of adhesion receptors to lower areas of asperities. Our measurement of the glycolyx stiffness (Fig. 2G), supports this assumption. Indeed, in presence of their native glycolyx, PC12 cells interact predominantly with the apical part of the nanotopographical asperities [9].

However, very little is known on how these two essential factors at the cell/microenvironment interface, the nanotopography and the glycolyx, affect nanoscale mechanotransductive processes in combination.

We were interested in modelling the accessibility of nanotopographical asperities for the cell in dependency of cell membrane compliance with the substrate, and how this would affect the corresponding configuration of the cell/substrate interface (Fig. 3B). We analysed morphological AFM maps of ns-Zr15 and ns-Zr20 by measuring, at different interfacial depths, several parameters that are significant for cell adhesion and mechanotransduction (Fig. 3C,D). Into this model, we incorporated known mechanotransduction-relevant factors, such as ligand spacing and minimal adhesion unit (for details on the model, see Methods “[Modelling of the surface accessibility in dependency of the cell membrane compliance](#)”). For ligand spacing, we set a value of 60 nm, based on the identified threshold that regulates the formation of IAC

[42–44]. In addition, Changede et al. [45] found that nanocluster bridges of unligated integrins can form between adjacent (tens of nm) nanometric adhesion sites which alone are not sufficient to sustain IAC maturation. With respect to the minimal adhesion unit, we determined the number of those asperities at the different interfacial depths that are characterised by a 3D surface area of at least 3600 nm<sup>2</sup>, because it has been shown that, at least, four integrin binding sites within 60 nm can serve as such a minimal adhesion unit that promotes IAC maturation [45–48].

The objective behind this modelling was to get an idea of the kind of nanotopographical cues the cell might perceive at different levels of compliancy (Fig. 3C). The morphological differences between nanotopographical substrates have the potential to shift spatial mechanotransduction-relevant factors, as we have previously shown in a simpler model [9]. However, the disordered nature and complex geometrical properties of these nanostructured asperities prompt an in-depth analysis considering also the cell membrane compliancy, because integrin clustering depends on the local arrangement of adhesion sites at the nanoscale rather than on the global average ligand density [49].

The number of accessible asperities initially increases for both conditions, ns-Zr15 and ns-Zr20, when reaching deeper interfacial depths, but deeper compliancy levels are necessary for ns-Zr15. Also, the mean area of these asperities and the total 3D surface area is lower for ns-Zr15 than for ns-Zr20 at most compliancy levels (except for very low compliancy) (Fig. 3C, D). Consistently, after the integration of the ligand spacing factor, the convergence of asperities which are in a 60 nm adjacency can only be achieved at much higher compliance level for many asperities in the ns-Zr15 condition, as well as the spatial requisites for minimal adhesion unit (Figs. 2B, 3C, D).

These results demonstrate, as expectable, that stronger cell membrane compliance to the nanotopographical surface can provide an increased number of interaction sites with spatial conditions that are suitable for integrin

clustering and IAC maturation. These specific effects are, however, highly dependent on the given roughness of the nanostructured zirconia substrate. Indeed, a counterintuitive property of these cluster-assembled zirconia interfaces is that the rougher ns-Zr20 substrates display properties, in terms of mechanotransduction-relevant parameters, that are closer to the flat surface situation (which has no spatial restrictions) over a wide range of compliance levels; i.e., a potentially less strict confinement of interaction areas for integrin adhesion. The model predicts instead a stark difference of mechanotransduction-relevant parameters between the low (corresponding to the presence of native glycocalyx) and higher compliancy level (reduced glycocalyx) for the ns-Zr15 substrate.

The model suggests that the nanotopographical cues appear as a kind of “3D QR code” (Fig. 3C) whose read-out will be affected by the ability of the cell membrane to reach lower parts of the asperities. Divergent levels of cell membrane compliance will provide different spatial surface information to the cell, with the potential to influence mechanotransductive nanoscale processes, such as force loading and molecular clutch engagement.


#### Adhesion Force Spectroscopy for the characterisation of the impact of the nanotopography and glycocalyx on early integrin-related interactions

It has been demonstrated previously that spatial restrictions of the cellular adhesion site dimensions at the nanoscale (as in the case of ns-Zr15) keep IAC at the focal complex size and diminish stress fibre development, compared to featureless flat substrates on which the IAC mature to FA and stress fibres form [9]. Recently, we have also shown that interaction with these specific nanotopographical features can cause excessive force loading in integrin-mediated nanometric adhesion sites during nascent adhesion formation, leading to their disassembly, regulated by availability of activated integrins [16].

Here, we analysed how the adhesion and force loading dynamics towards different nanotopographical features


(See figure on next page.)

**Fig. 4** Differences in the nanotopography can induce specific adhesion dynamics that strongly depend on the glycocalyx configuration. The panel shows the results of the adhesion force spectroscopy measurements for probes with flat-zirconia films devoid of nanotopographical features (flat-Zr, blue lines or bars), and with nanostructured cluster-assembled zirconia films with a roughness  $R_q$  of 15 nm (ns-Zr15, red lines or bars), or 20 nm (ns-Zr20, black lines or black/grey bars), in the presence of the cell's native glycocalyx (solid lines or bars), or after glycocalyx reduction by enzymatic digestion (dashed lines or bars with border lines). The measurements were taken at 5 different cell-probe contact times (0 s, 20 s, 60 s, 120 s, and 240 s). The parameters presented in this graph are **A** Maximum adhesion force  $F_a$ , **B** Number of jump bonds  $N_j$ , and **C** Mean strength of jump bonds  $\langle F_j \rangle$  (Work  $W$  and Number of tether bonds  $N_t$  can be found in Additional file 1: SI – SI Fig. S6). The error bars represent the effective standard deviation of the mean details in 4.3.4). Asterisks indicate significant differences between control and glycocalyx-targeting enzymatic treatments. **D** The bars show the temporal evolution of the jump force distributions for the different experimental conditions, allocating the forces into 3 categories, i.e. low forces < 50 pN, intermediate forces, 50–100 pN, high forces > 100 pN (the original distributions of bond strength can be found in the Additional file 1: SI – SI Fig. S7, to see the dispersion of higher forces

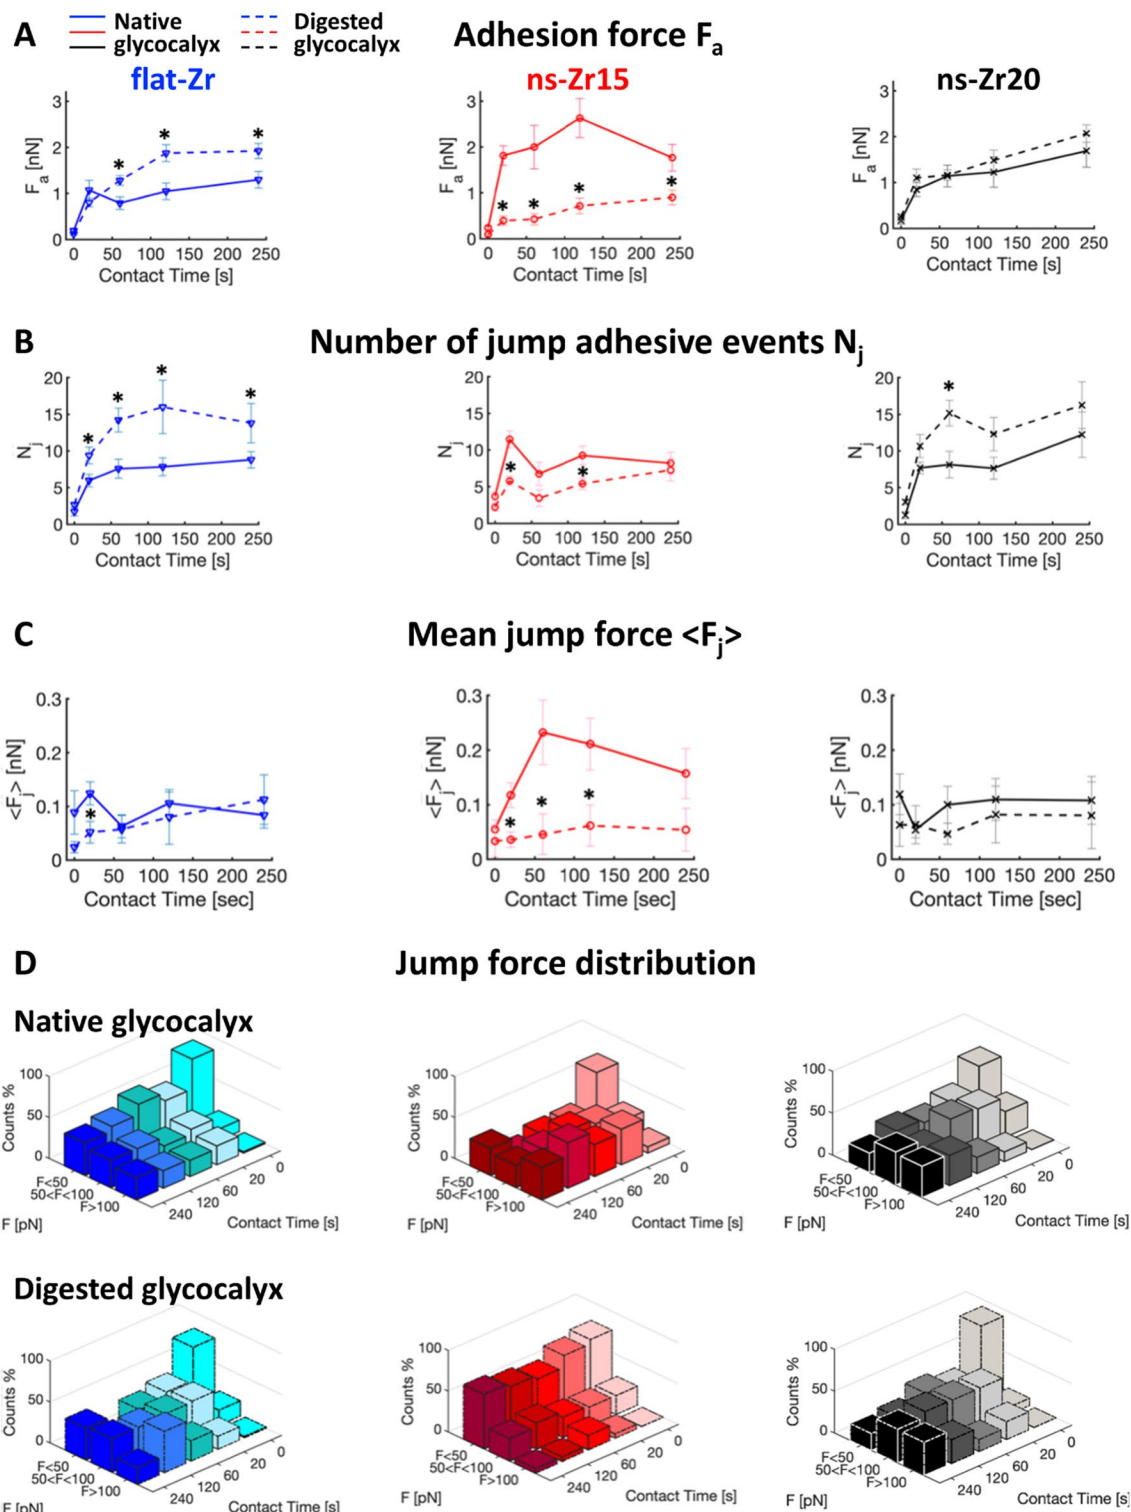

**Fig. 4** (See legend on previous page.)



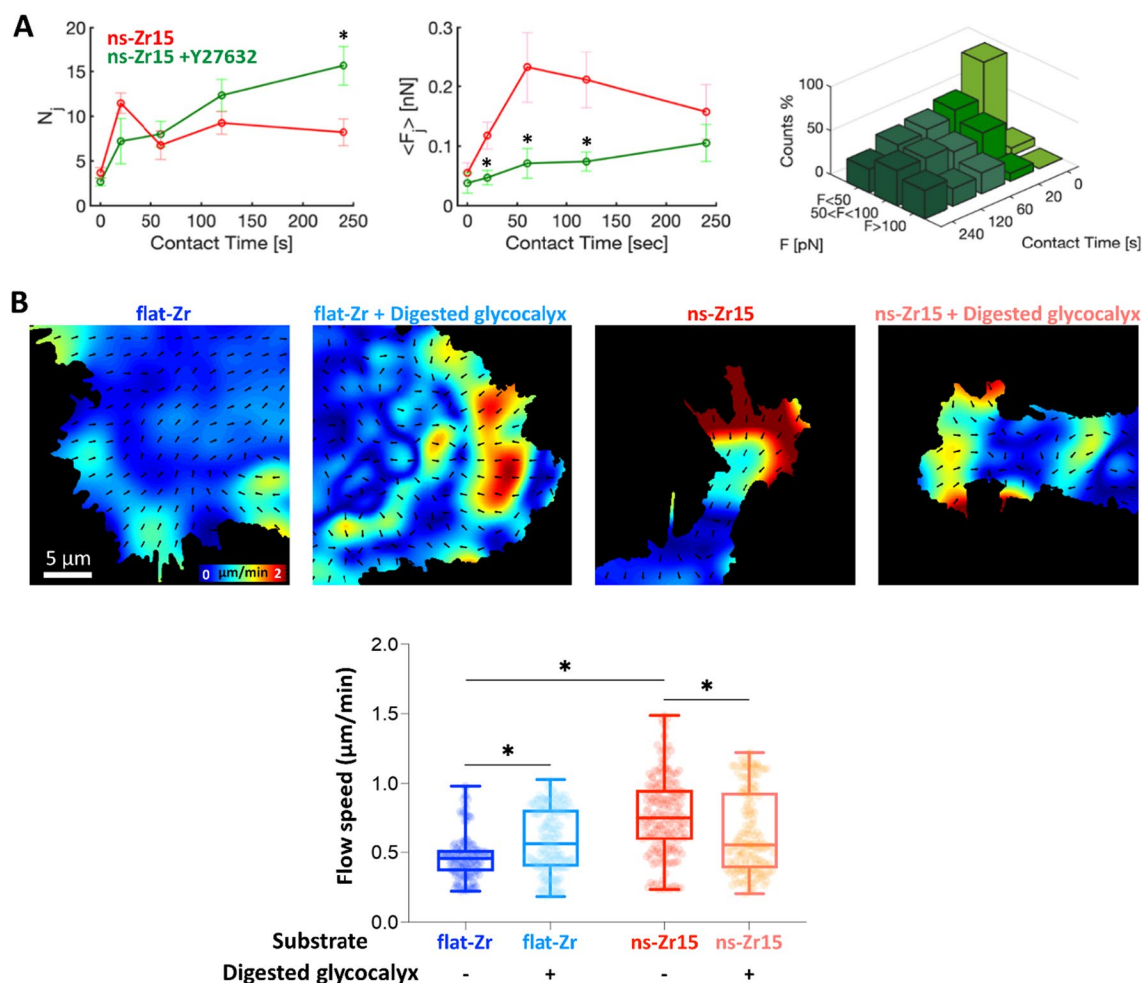

**Fig. 5** The nanotopography and the glycoalyx configuration affect the lamellipodial molecular clutch engagement and actin dynamics. **A** The graphs summarise the evolution of  $N_j$ ,  $\langle F_j \rangle$  and jump force distribution comparing untreated PC12 cells interacting with ns-Zr15 (red lines, reproduced from Fig. 4B,C), or treated the ROCK inhibitor Y27632 (10  $\mu\text{M}$ , green lines or bars, for ns-Zr15 Native glycoalyx jump force distribution, compare with Fig. 3D). The error bars represent the effective standard deviation of the mean (details in 4.3.4). Asterisks indicate significant differences between control and Y27632 treatment. **B** The panel shows representative actin flowfield images obtained after Particle Image Velocimetry (PIV) of live cell recordings of PC12 cells (transfected previously with LifeAct<sup>TM</sup>-mCherry to visualise the actin dynamics) in the different experimental conditions (corresponding videos can be found in the SI). The confocal recordings had a frame rate of 0.5 images/sec. The graph below shows the according PIV-based quantification of the actin dynamics. The boxplots show medians, 25th and 75th percentile as box limits. 198–234 frames from 11–14 cells/lamellipodial zones were quantified. A Kruskal–Wallis statistical test was applied with multiple comparisons (flat-Zr native glycoalyx vs. after glycoalyx digestion, ns-Zr15 native glycoalyx vs. after glycoalyx digestion, flat-Zr vs. ns-Zr15 native glycoalyx, flat-Zr vs. ns-Zr15 after glycoalyx digestion). \*  $p < 0.0001$

change in the presence or after major digestion of the glycoalyx (Fig. 4).

We therefore performed adhesion force spectroscopy [16] on PC12 cells with their native glycoalyx and after treatment with glycoalyx-targeting enzymes. We used colloidal probes coated with three different topographies: flat-Zr, ns-Zr15, and ns-Zr20 (typical representations of the morphological probe features are shown in Additional file 1: SI - Fig. S5). We selected five cell-probe contact times covering different stages of the critical

window of nascent adhesion formation towards maturation to focal adhesions [50, 51], i.e. 0 s, 20 s, 60 s, 120 s, and 240 s.

From these measurements we derived information on the maximum adhesion force  $F_a$  (Fig. 5A), the number of jumps  $N_j$  (Fig. 5B), the mean jump force  $\langle F_j \rangle$  (Fig. 5C), the distribution of jump force (Fig. 5D), the work  $W$  (Additional file 1: SI - Fig. S6A), and the number of tethers  $N_t$  (Additional file 1: SI - Fig. S6B). Jump events are usually associated with membrane adhesion receptors

**Table 1** Most probable jump forces at 0 s

Topography/ experimental condition	Native glycocalyx	Digested glycocalyx
flat-Zr	44 ± 16 pN	25 ± 18 pN *
ns-Zr15	39 ± 16 pN	28 ± 10 pN *
ns-Zr20	43 ± 17 pN	33 ± 11 pN *

The table shows the most probable jump forces at 0 s for the different experimental conditions.

\* indicate significant differences between control and glycocalyx-targeting enzymatic treatments

that are anchored to the cytoskeleton, as for integrins engaged in molecular clutches [52–55], while the tether events are attributed to receptors that are not bound to the cytoskeleton [56, 57].

#### **Nanoscale differences in the topography modulate the temporal adhesion and force loading dynamics**

We first analysed the impact of the three different topographies in the presence of the native glycocalyx (solid lines in Fig. 4). The results for flat-Zr and ns-Zr15 closely reproduced the outcome of our previous work [16]. The adhesion force  $F_a$  was generally low in the flat-Zr condition, and the number of jumps  $N_j$  increased progressively until reaching a plateau. A different situation was found for the ns-Zr15 condition, where  $F_a$  reached higher values and  $N_j$  fluctuated heavily, i.e., first increasing strongly at 20 s and then showing a drop towards 60 s. This was reflected in a significant divergence of mean jump strength  $\langle F_j \rangle$  for the two conditions. Whereas this value had only minor variations in the flat-Zr condition, a rise to higher values in the ns-Zr15 condition with a maximum at 60 s was observed. Generally, the range of  $N_j$  values at later time points are in good accordance with the potential adhesion sites predicted by the model after integrating the ligand spacing factor (compare Fig. 3C,D with Fig. 4B).

Interestingly, the values for ns-Zr20 condition were instead akin to the flat-Zr condition, and not to the ns-Zr15 one, in agreement with the model predictions: a smooth increase in  $F_a$  with low absolute values comparable to those obtained on flat-Zr, and a constantly low  $\langle F_j \rangle$ . The values for  $W$  and  $N_t$  wavered in a similar range for all three conditions (Additional file 1: SI - Fig. S6, solid lines). A dissection of the jump force distribution (Fig. 4D) showed for flat-Zr that most jump forces were in the <50 pN category at all time points, with only a minor increase of intermediate (50–100 pN) and higher forces (>100 pN) over time. For ns-Zr15, there was instead an early shift (starting already at 20 s) towards the higher forces,

i.e., >100 pN, even with appearance of some very high forces. The ns-Zr20 condition was intermediate, the jump force distribution was more equilibrated than in the other two conditions, with the 50–100 pN category being the predominant one for most time points (except 120 s).

These data show that small differences in nanoscale topographical features can have a significant effect on early cellular adhesion parameters and interfacial force-related mechanotransductive processes at the cell membrane level.

#### **The configuration of the glycocalyx impacts on the mechanosensing of the nanotopography**

After digestion of the glycocalyx, some interesting and divergent effects could be observed (dashed lines in Fig. 4 and Additional file 1: SI - Fig. S6).

For the ns-Zr15 condition, the major glycocalyx reduction had a strong impact on several parameters: it reduced  $F_a$ ,  $N_j$ ,  $\langle F_j \rangle$  and  $W$  to values that were actually very similar to those we observed for the flat-Zr condition with the native glycocalyx, or even below, from 20 s onwards.

For the flat-Zr condition, the digestion of the glycocalyx had instead the opposite effect for  $F_a$  and  $N_j$ , leading to increased values that are comparable to the ns-Zr15 situation with the native glycocalyx or even higher, whereas  $W$  and  $\langle F_j \rangle$  (except 120 s) remained basically unchanged. For ns-Zr20, the variations due to the glycocalyx-targeting enzymatic treatment were more modest, the  $W$  (for the 120 s and 240 s time points) and  $N_j$  (at 60 s) increased at certain time points, whereas  $F_a$  and  $\langle F_j \rangle$  did not alter. The strong cutback of the glycocalyx had a drastic effect on the jump force distribution (Fig. 4D) in the ns-Zr15 condition, as most of the jump forces were found in the <50 pN category for all time points. A minor fraction of forces was in the 50–100 pN category, whereas higher forces were practically absent. This was an almost complete inversion compared to the untreated cells interacting with this nanotopographical surface. The glycocalyx-targeting treatment had instead little impact on the jump force distribution in the flat-Zr condition (slight shift to more intermediate forces) and there was almost no alteration for ns-Zr20 condition.

An interesting aspect was also observed with respect to the most probable jump forces at 0 s. The values for these first pristine interactions forming between integrins and substrate were reduced after glycocalyx digestion in all topographical conditions (Table 1, see also Additional file 1: SI - Fig. S7). This is congruent with the mechanical loading of integrins due to the adjacent compressed glycocalyx shown by Paszek et al. [18, 41], and our data on the glycocalyx stiffness (Fig. 2G).

These results show that the glycocalyx has a decisive influence on the early adhesion dynamics towards nanotopographical features and that this influence depends on the nanometric details of the topography, as evident especially for the case of ns-Zr15 (which has been shown to strongly modulate IAC-mediated mechanotransductive processes and signalling in PC12 cells [9, 10, 16]). Indeed, the impact of glycocalyx reduction can strongly differ in dependency of the particular nanotopographical conditions, as also suggested by the model.

#### **The glycocalyx configuration affects nanotopography-sensitive molecular clutch engagement to the retrograde actin flow**

The forces that drive the force loading within molecular clutches derive from the retrograde actin flow in lamellipodia, which, in turn, is generated by actin polymerisation and actomyosin contraction, regulated by Rho/ROCK signalling [1, 2, 5, 6, 58–66]. An inverse relationship between actin retrograde flow velocity and the traction forces has been demonstrated during transition from nascent adhesion to FA, i.e. IAC maturation causes actin flow deceleration by molecular clutch engagement and reinforcement [60–62, 64].

For flat substrates, it is known that the initial integrin clustering in nascent adhesions is independent of actomyosin-driven forces [60, 67]. The force loading in molecular clutches, IAC growth to FA, and stress fibre formation, instead strongly depend on actomyosin contraction.

To understand whether the observed nanotopography-sensitive force loading dynamics in the nascent adhesions depend on actomyosin-driven contractility, force spectroscopy measurements with the ns-Zr15 probes on PC12 cells treated with the ROCK inhibitor Y27632 have been performed. The results revealed a clear change of the adhesion dynamics and forces after the Y27632 treatment (Fig. 5A). Differently from the ns-Zr15 condition of untreated cells,  $N_j$  progressively increased over time after the inhibition of the actomyosin contraction, reaching particularly high levels at 120 s and 240 s. Compared to the untreated ns-Zr15 condition,  $\langle F_j \rangle$  was strongly reduced for the time points in the critical nascent adhesion formation window (20 – 120 s), with appearance of fewer high forces. Also, the most probable jump force at 0 s was reduced ( $25 \pm 14$  pN, compared to the value of untreated cells reported in Table 1, i.e.,  $39 \pm 16$  pN). These data indicate the importance of driven forces for the specific ns-Zr15 adhesion force dynamics.

Lamellipodia are integrators of the biophysical cues that are present in the local cellular microenvironment. To that effect, the lamellipodial retrograde actin flow velocity is a good indicator for the overall force loading-dependent


molecular clutch engagement induced by a specific substrate [1, 2, 4, 6, 59]. Basically, the retrograde actin flow changes as a function of the configuration and overall maturation status of the IACs inside the lamellipodia. To test how the nanotopographical substrate cues and the glycocalyx configuration are integrated in a more long-term and comprehensive adhesion scenario, we measured the retrograde actin flow speed (and accordingly the extent of molecular clutch engagement), by recording the actin cytoskeletal dynamics (visualised by LifeAct<sup>TM</sup> transfection) of PC12 cells that interact with flat-Zr or ns-Zr15 substrates in the presence or after digestion of the glycocalyx.

Particle image velocimetry (Fig. 5B and corresponding videos) demonstrated that the lamellipodial actin flow dynamics were significantly faster in the cells plated on ns-Zr15, compared to flat-Zr. This is in good accordance with the fact that on ns-Zr15 the IAC have focal complex dimensions due to the nanotopography-imposed spatial restriction for integrin nanocluster formation, whereas there is focal adhesion formation on flat-Zr [9]. This nanotopography-dependent difference in actin flow speed equals when the cells were treated with the glycocalyx-targeting enzymes, meaning that the actin flow speed increased on flat-Zr and decreased on ns-Zr15.

Notably, the opposite effect on the retrograde actin flow, due to major glycocalyx reduction, that was observed between flat-Zr and ns-Zr15, which represents a more comprehensive adhesion effect, is congruent to the phenomena seen for the nascent adhesion force dynamics in the force spectroscopic measurements. These data demonstrate that the nanotopography mechanosensing relies on Rho/ROCK signalling-regulated actomyosin contraction and that molecular clutch engagement is nanotopography-sensitive in a glycocalyx-dependent manner.

For flat-Zr, the effects of the glycocalyx digestion are in good accordance with the paradigm established by Paszek et al. [18, 41], i.e., a bulky glycocalyx layer promotes integrin clustering by funnelling of active integrins to an initial integrin/ligand binding site (“kinetic trap”) and by applying additional tension due to upward force caused by the adjacent glycocalyx compression. The force spectroscopy results suggest that the glycocalyx’ steric repulsion indeed strengthens the initial bonds, and that, after strong reduction of the glycocalyx, the cells create more bonds with the microenvironment. However, the increase in the actin retrograde flow speed after glycocalyx digestion indicates that abolition of the glycocalyx-dependent effects reduces the molecular clutch engagement and integrin clustering on the flat substrate.

Nanotopographical features apparently add another level of complexity, leading to particular glycocalyx-sensitive

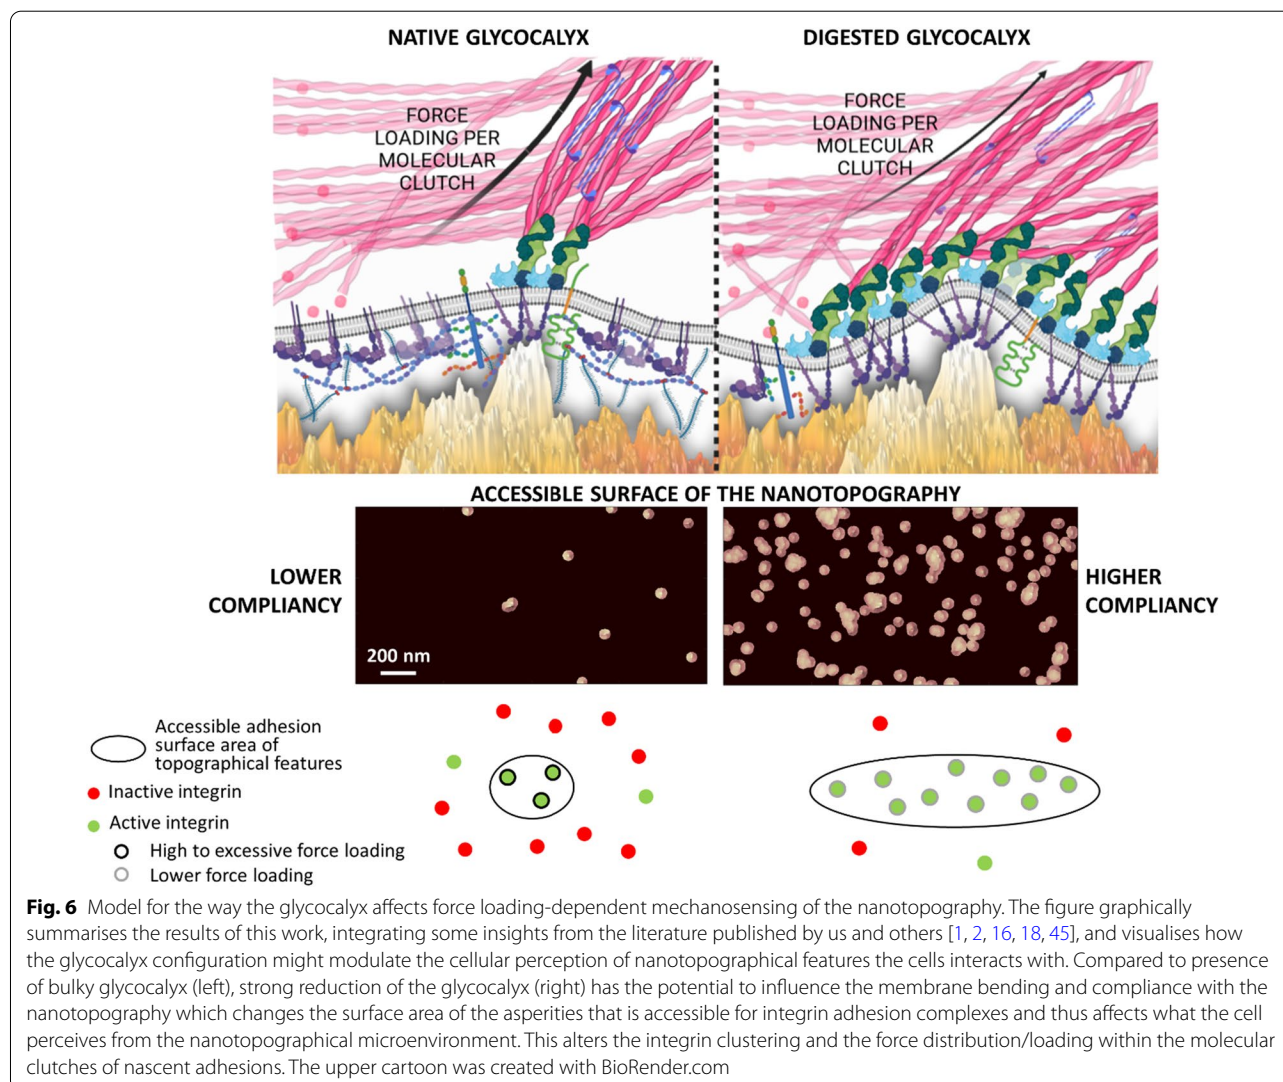

**Fig. 6** Model for the way the glycocalyx affects force loading-dependent mechanosensing of the nanotopography. The figure graphically summarises the results of this work, integrating some insights from the literature published by us and others [1, 2, 16, 18, 45], and visualises how the glycocalyx configuration might modulate the cellular perception of nanotopographical features the cells interacts with. Compared to presence of bulky glycocalyx (left), strong reduction of the glycocalyx (right) has the potential to influence the membrane bending and compliance with the nanotopography which changes the surface area of the asperities that is accessible for integrin adhesion complexes and thus affects what the cell perceives from the nanotopographical microenvironment. This alters the integrin clustering and the force distribution/loading within the molecular clutches of nascent adhesions. The upper cartoon was created with BioRender.com

phenomena that are subject to the exact topographical configuration, as they are specific for the ns-Zr15 condition. In the presence of the native glycocalyx, the initial nascent adhesion formation, which is independent of actomyosin contraction, seems to be promoted in the ns-Zr15 condition (high  $N_j$  towards 20 s). However, the excessive force loading-dependent events (increase of  $\langle F_j \rangle$  and drop of  $N_j$ , which are dependent on actomyosin contraction) lead eventually to a lower molecular clutch engagement to the retrograde actin flow (higher speed compared to the flat-Zr condition). Concordantly, we know from our previous work that the IAC are of much smaller nanometric dimensions (focal complex size) on ns-Zr15, compared to the micrometric FA on flat-Zr [9]. The deceleration of the retrograde actin flow speed, after glycocalyx digestion, insinuates instead an increased molecular clutch engagement compared to control ns-Zr15 condition.

Strong glycocalyx reduction has the potential to increase the accessible surface contact area [14], by enabling easier membrane bending around the asperities due to the omission of the repulsive forces of the compressed glycocalyx [2, 18] (Fig. 3C,D, Fig. 6). The differences between ROCK inhibition and glycocalyx removal for the ns-Zr15 situation, especially regarding  $N_j$  (compare Fig. 5A and Fig. 4B), indicate a complex contribution of the glycocalyx configuration in nanotopography sensing.

## Conclusions

Our results shed some light on how the glycocalyx affects the cellular perception of nanotopographical features and impacts mechanotransductive events at the nanoscale.

Altogether, our data clearly demonstrate that the glycocalyx decisively modulates the dynamics of cellular

adhesive and mechanotransductive processes in a nanotopography-dependent way, particularly in regards with the number and structuring of adhesion sites at the nanometric scale and the force distribution within them. We show that the nanotopography and glycocalyx represent crucial factors within the cell/microenvironment interface that must be considered in mechanotransduction in an interdependent manner. The configuration of the glycocalyx and further intrinsic cellular parameters, such as the type and availability of activated integrins, and the extent of engagement to actomyosin-driven forces, control how a cell perceives the nanotopographical features it interacts with. We have demonstrated, for PC12 cells, how manipulations of the glycocalyx, integrin activation and actomyosin contraction change the topography mechanosensing at the nanoscale. As a function of these intrinsic (extra)cellular factors, the same nanotopography can convey diverse cues to the cell (Fig. 6).

Di Cio et al. [68] found, similar to our results, that cells became insensitive to the width of nanotopographical features (in their case nanofibers) upon ROCK inhibition. They suggest an actin architecture-dependent long-range, rather than FA-dependent, mechanism for nanotopography sensing, based on actin network collapsing into foci.

Differently to Di Cio et al., we here propose a molecular clutch force loading-dependent mechanism for nanotopography sensing, with a decisive involvement of the glycocalyx. The effect of the ROCK inhibition on the nanotopography sensing (through its impact on the force loading), i.e., that the cells become blind for the nanotopographical differences, has some similarities to the role of actomyosin contraction (by sarcomere-like contractile units) and force production in the rigidity sensing mechanism described by Wolfenson et al. [69, 70]. They have shown that the rigidity sensing occurs by actomyosin-driven stepwise contractions. These contractions in themselves are independent of the substrate rigidity and non-mechanosensitive [71], but a force threshold of around 20–25 pN has to be reached to enable IAC reinforcement [69].

Albeit the substrates we used here are rigid, we have shown that these nanotopographies can directly affect the extent of integrin clustering and the IAC size at the nanoscale [9], as well as the force loading in molecular clutches [16]. On ns-Zr15, the effects on mechanotransduction resemble what can be observed on soft substrates [1, 2, 58, 72]. Considering the work of Oria et al. [59] that points out the importance of the force loading in molecular clutches for spatial ligand sensing, the rigidity and nanotopography mechanosensing are likely to be interdependent. Our data strongly indicate that the

glycocalyx and the nanotopography configuration must be taken into account, as alterations therein can change the whole setting in the cell/microenvironment interface.

The dynamic biophysical cue-dependent events in the cell/microenvironment interface exhibit an intriguing complexity. Understanding the mentioned interdependencies in more detail will be a challenging and very interesting field for future investigations and it is of high biomedical relevance, in particular with respect to cancer cell biology [15, 21, 24, 70, 73–75].

It can be speculated that these general mechanisms in the cell/microenvironment interface might be similar for many cell types. Specific adhesion and force loading dynamics towards nanotopographies will certainly differ, depending on the cell type-specific glycocalyx thickness and composition, integrin expression levels, integrin trafficking, the contractile machinery, cytoskeletal organisation and mechanics. One of our future objectives will be to dissect such differences (or find similarities in patterns) between cell types, and/or between healthy and pathophysiological situations.

The potential implications of these cell/microenvironment interfacial processes for pathophysiological situations become evident from the fact that aberrations in the components along the mechanotransductive sequence have been associated with various diseases [76], particularly to cancer and metastasis, as well as neurodegenerative diseases [21, 73–75, 77, 78]. Examples are abnormal rearrangements and composition of the ECM [79–81] and glycocalyx [82], as well as dysregulation in IAC-related genes [83, 84], or in the contractile machinery [75]. Recently, it has been shown that a glycocalyx-dependent potentiation of an integrin-mediated mechanosignalling feedback loop might be causally involved in the primary brain cancer glioblastoma multiple [85].

Here we concentrated on direct integrin-mediated mechanotransduction, but these results could have also broader relevance in the context of other surface receptors (such as syndecan-4 [86], CD44 [87], uPAR [64, 88]), receptor clustering in synaptic perineuronal nets [89], and curvature-sensing proteins (such as FBP17) [90].

Obtaining a deeper understanding of the nanoscale mechanotransductive events at the cell/microenvironment interface is thus essential. It is furthermore highly attractive from a biomedical, diagnostic and therapeutic perspective because the cellular outside and surface are easier to access than intracellular processes. This manifests in a recent re-evaluation and emergence of interest in potential ECM- and integrin-targeting drugs, or more general, so-called mechanotherapeutics [77, 81, 91, 92].

## Materials and methods

### Fabrication and calibration of the colloidal probes

The procedure for the fabrication of colloidal probes (CP) is based on the approach described elsewhere [93, 94]. The most important highlights of the protocol and the advantages of the probes that can be produced are reported below.

A borosilicate glass sphere (Thermo fisher Scientific), with nominal radii  $R=5\ \mu\text{m}$  for nanoindentation (see "Glycocalyx characterisation by AFM nanoindentation") and  $R=10\ \mu\text{m}$  for adhesion spectroscopy (see "Morphological characterisation of surfaces (substrates and cells)"), is attached to a tipless silicon cantilever (Micromash HQ:CSC38/tipless/no Al, spring constant  $k=0.02\text{--}0.03\ \text{N/m}$ ) exploiting capillary adhesive forces or a small amount of vaseline as temporary adhesive. The glass sphere is then covalently attached to the silicon cantilever by thermal annealing for two hours in a high-temperature oven at the softening point temperature ( $T=780\ ^\circ\text{C}$ ). The resulting monolithic colloidal probe can be washed/cleaned aggressively after use in order to remove contaminants. The characterisation of the CP radius is performed by atomic force microscopy (AFM) reverse imaging of the probe on a spiked grating (TGT1, Tips Nano), as detailed in Indrieri et al. [93]. The spring constant is calibrated using the thermal noise method [95, 96] where special correction factors are applied in order to take into account the relevant dimension and mass of the glass sphere [94, 97].

### Production of nanotopographical probes and substrates

For the production of the nanotopographical CPs (for adhesion force spectroscopy) and for the nanostructured substrates (for the retrograde actin flow experiments), ns-ZrO<sub>2</sub> films are deposited on the colloidal probes, or glass substrates, respectively, exploiting the Supersonic Cluster Beam Deposition (SCBD) technique (described in detail in the Refs [26, 98, 99]). Briefly, SCBD allows the production of nanostructured surfaces characterised by a disordered topography, yet with accurately controllable and reproducible morphological properties such as rms roughness, cluster size distribution and porosity [100–102]. Partially oxidised zirconia clusters are produced within the cluster source and then extracted into the vacuum of the expansion chamber through a nozzle to form a seeded supersonic beam. Clusters are collected directly on the CPs, or glass substrates, intercepting the beam in the deposition chamber. Upon landing on the sample surfaces, clusters form a nanostructured, highly porous, high-specific area, biocompatible ns-ZrO<sub>2</sub> film [27, 32]. The protocol for the functionalisation of the colloidal probes with the nanotopographical surfaces achieved

by zirconia cluster-assembling is detailed in Chighizola et al. [16]. The specific surface area, the rms roughness (defined as the standard deviation of the height of the surface,  $r_q = \sqrt{\frac{1}{N} \sum_i (h_i - \bar{h})^2}$ , where  $h_i$  is the height of the surface in a specific point,  $N$  is the number of pixels of the map and  $\bar{h}$  is the average height), the average lateral dimensions of the largest morphological features (the correlation length  $\xi$ ) typically increase with ZrO<sub>2</sub> film thickness [100, 102, 103].

### AFM experiments

All the AFM experiments have been performed using a Bioscope Catalyst AFM (Bruker), mounted on top of an inverted optical microscope (Olympus X71). Isolation of the system from noise was obtained by means of both, an active anti-vibration base (DVIA-T45, Daeil Systems), and an acoustic enclosure for the AFM (Schaefer, Italy). During the AFM measurements performed on live cells, the temperature of the cell culture medium was maintained at  $37\ ^\circ\text{C}$  using a perfusion stage incubator (PSI, Bruker) and a temperature controller (Lakeshore 331, Ohio, USA). Before every measurement the deflection sensitivity was calibrated in situ and non-invasively by using the previously characterised spring constant as a reference, according to the SNAP procedure described in Schillers et al. [104] and based on the assumption that the correct deflection sensitivity value must provide, through the noise calibration, the reference value of the spring constant. The cell regions to be investigated (portion of the membrane to be scanned or location of the force curves to be acquired) were chosen by means of the optical microscope; the accurate alignment of the optical and AFM microscopes was obtained using the Miro (Bruker) module integrated in the AFM software. Data processing of the sets of curves and scan images was carried out in Matlab (Mathworks) environment using custom routines.

### Morphological characterisation of surfaces (substrates and cells)

Morphological images of nanostructured zirconia thin films deposited on colloidal probes were acquired with a Bioscope Catalyst AFM (Bruker), in tapping mode. NCHV probes from Bruker, with resonance frequency about 300 kHz, force constant  $k=40\ \text{N/m}$ , and nominal tip radius 10 nm, were used for these experiments. The topographic maps have been collected with a sampling resolution of  $1\text{--}2\ \text{nm/pixel}$  using as scan rate of 1 Hz.

For the morphological surface characterisation of the PC12 cells, the cells were fixed with 2% paraformaldehyde/0.1% glutaraldehyde in PBS for 30 min (fixation protocol from Zeng et al. [105]) after 1 day of culturing on poly-L-lysine (PLL)-coated (0.1% w/v PLL solution (Sigma) for 30 min at RT) glass-bottomed plates

(Willco Wells). The fixed cells were characterised using a Bioscope Catalyst AFM from Bruker. The AFM images (with scan size of 3–5  $\mu\text{m}$ ) were acquired in PBS buffer in peak-force tapping mode. Because of the significant height variations within the samples (up to several micrometres), cantilevers with a tip height of 14  $\mu\text{m}$  were used (VistaProbes CS-10). The scan rate was set to 0.6 Hz, the ramp frequency at 1 kHz, and the sampling resolution was set to  $4096 \times 1024$  points. To avoid degradation of the glycocalyx, the measurements were performed within max. 24 h following the fixation. However, the fixation still bears a risk of artefacts, therefore the images were only used as a qualitative and visual illustration of the impact of the enzymatic treatment on the cell surface and glycocalyx configuration, which was furthermore in good agreement with the quantified effects by the methods describe in 4.3.3 and 4.5.

#### Adhesion force spectroscopy and data analysis

Adhesion force spectroscopy measurements were performed as discussed in detail in Chighizola et al. [16]. The nanotopographical colloidal probes ( $R=10 \mu\text{m}$ ) were incubated with the cell culture medium ( $\emptyset$  phenol red) for  $>30$  min at  $37^\circ\text{C}$  before the actual measurements (to guarantee absorption of ECM proteins, such as fibronectin and vitronectin, present in the serum to the probes). Sets of force-distance curves were acquired at locations on the cells' body selected by means of the optical microscope. Force curves (FCs) containing 8192 points each were recorded on live PC12 cells, with ramp length  $l=10 \mu\text{m}$ , maximum load  $F_{max}=1 \text{ nN}$  and retraction speed at  $v_r=16 \mu\text{m/s}$ . The pulling speed was kept relatively low to reduce hydrodynamics effects [106]. To measure the early steps of cellular adhesion in the critical phase of nascent adhesion formation towards FA maturation, we selected five contact times (*cts*): 0, 20, 60, 120, 240 s, accordingly. During the contact time, the Z-piezo position was kept constant using the Z closed-loop feedback mode. The data analysis of the retraction curves was carried out using the protocol presented in Chighizola et al. [16].

#### Glycocalyx characterisation by AFM nanoindentation

**Glycocalyx thickness** Nanomechanical indentation experiments were performed using colloidal probes with radius  $R=5 \mu\text{m}$  following the approach presented by Puricelli et al. [107]. To get quantitative information about the thickness of the glycocalyx, we applied the brush model implemented by Sokolov et al. [34, 35]. This model was developed with the purpose to decouple the single mechanical contributions of the glycocalyx compression and the underlying cell deformation, allowing isolating the force needed to compress the glycocalyx (for details,

see Additional file 1: SI2 and Additional file 1: SI – Fig. S2-3).

**Glycocalyx stiffness** Mechanical properties of the glycocalyx were calculated following the approach described by Wiesinger et al. [108]. The effective glycocalyx spring constant or stiffness, defined following the Hook's Law  $K_{GC} = dF/dh$  has been extracted from each FC by selecting a suitable small region where the entropic resistance to compression [34] can be considered linear.

#### Statistics and error analyses

For each observable  $\psi_{FC}$  extracted by each force curve (FC) (e.g., the adhesion force  $F_a$ , the work  $W$ , the GC stiffness  $K_{GC}$ ), a mean value  $\bar{\psi}_{cell,j}$  was evaluated for each cell:

$$\bar{\psi}_{cell,j} = \frac{\sum_{i=1}^{n_j} \psi_{FC,i}}{n_j}$$

where  $n_j$  is the number of FCs per each cell,  $j=1, \dots, N$ ,  $N$  being the number of cells investigated for each condition.

The mean value  $\bar{\psi}$  representative of the cell population in each condition was evaluated as:

$$\bar{\psi} = \frac{\sum_{j=1}^N \bar{\psi}_{cell,j}}{N}$$

The effective error  $\sigma_{\bar{\psi}}^*$  associated to  $\bar{\psi}$  was obtained by summing in quadrature the standard deviation of the mean  $\sigma_{\bar{\psi}} = \sigma_{\psi} / \sqrt{N}$ ,  $\sigma_{\psi}$  being the standard deviation of  $\bar{\psi}_{cell,j}$  values, and an estimated instrumental error  $\sigma_{instruct}$  ( $\sigma_{instruct}/\bar{\psi} = 3\%$ ) [107]:

$$\sigma_{\bar{\psi}}^* = \sqrt{\sigma_{\bar{\psi}}^2 + \sigma_{instruct}^2}$$

#### Modelling of the surface accessibility in dependency of the cell membrane compliancy

The strategy used to determine the potential interacting interface of the cells in contact with nanotopographical surfaces, consists in analysing the morphological AFM maps ( $n=3$  per roughness value) of the cluster-assembled thin zirconia films (Fig. 3A), by applying masks at different interfacial heights (Fig. 3B,C).

The starting threshold in  $z$  was chosen from the value of the highest asperity of the morphological map, and we have decreased the subsequent thresholds by 5 nm per step (as schematically shown in Fig. 3A). For each threshold used, we mask the portion of the AFM image below the chosen threshold. For each threshold value, we calculated the number of asperities, the mean surface area of asperities, the sum of the 3D surface area of the asperities identified on the surface (total surface area),

the specific surface area (defined as the ratio of 3D area of the asperities and their projected 2D area), and the coverage (defined as the sum of the 2D projected area of the asperities identified over the entire 2D area).

In order to integrate the mechanotransductively-relevant parameter integrin ligand spacing, we have calculated the change in the number of zirconia asperities at each threshold by expanding the perimeter of the 2D area of each asperity of 30 nm in x–y direction, since 60 nm was identified as critical ligand spacing distance for the maturation of integrin adhesion complex [42–44]. Converging asperities were considered as connected adhesion areas and counted as a single entity. Furthermore, it was determined that, at least, four integrin binding sites in a vicinity of 60 nm can serve as a minimal adhesion unit which promotes IAC maturation [45–48]. For this reason, we analyzed also the number of asperities at different interfacial depths, characterised by a 3D surface area of, at least,  $60 \text{ nm} \times 60 \text{ nm} = 3600 \text{ nm}^2$ .

#### Cell culture and preparations for experiments

The experiments were performed with the neuron-like PC12 cells (PC12-Adh clone, ATCC catalogue no. CRL-1721.1TM). This cell line has shown to respond to the nanotopographical cues provided by the substrates produced by SCBD (in particular ns-Zr15) by mechanotransductive processes and signalling, which we have profoundly characterised in previous studies [9, 10, 16].

For routine cell culture (subculturing every 2–3 days using trypsin/EDTA solution), the PC12 cells were maintained (in a humid atmosphere at 37 °C and 5% CO<sub>2</sub>) in an incubator (Galaxy S, RS Biotech) provided with RPMI-1640 medium (supplemented with 10% horse serum, 5% fetal bovine serum, 2 mM L-glutamine, 10 mM HEPES, 100 units mL<sup>-1</sup> penicillin, 100 µg mL<sup>-1</sup> streptomycin, 1 mM pyruvic acid). All reagents and materials from Sigma, also in the following, if not stated otherwise.

For the experiments, the cell detachment was done on the day before with an EDTA (1 mM in PBS) solution to not digest the protein component of the glycocalyx. The cells were counted with an improved Neubauer chamber before plating them in a low concentration (4000 cells per cm<sup>2</sup>, to have mostly single, separated cells) on the indicated substrates. The cells were then maintained in the incubator overnight to guarantee good cell adhesion.

For the experiments involving AFM measurements, the cells were seeded the day before the experiment on Ø 40 mm glass-bottomed plates (Willco Wells) that were coated before with PLL (0.1% w/v PLL solution for 30 min at RT). Solutions without phenol red were used, as it results harmful for the AFM tip holder.

For the actin dynamics measurements, one day before the experiment the cells (after LifeAct™ transfection, see 4.6.1) were instead plated on Ø 35 mm glass-bottomed dishes (MatTek, the Ø 13 mm glass was in the centre of the plate) on which either flat zirconia film (produced by ion gun sputtering) or nanostructured cluster-assembled zirconia film (fabricated by SCBD) have been deposited.

In case of glycocalyx-targeting enzymatic treatment, an enzyme cocktail was applied to the cell culture medium to obtain a final concentration of 13.5 U/mL hyaluronidase II, 150 mU/mL chondroitinase ABC, 300 mU/mL heparinase III and 150 mU/mL neuraminidase (these concentrations were inspired by the work of Zeng et al. [105]). The cells were incubated with these enzymes for 2 h right before the experiments. Following the incubation, the cell culture medium was discarded. After washing 3 × with PBS (to remove the digested glycocalyx), fresh medium was added containing again the enzymatic cocktail to avoid reassembly of the glycocalyx during the measurements.

For the Y27632 inhibition against ROCK, the cells were pre-incubated with the inhibitor 15 min before the measurements. During the measurements the inhibitor remains present in the medium. The inhibitor was used at a final concentration of 10 µM.

#### Glycocalyx characterisation by wheat germ agglutinin staining and 3D-Structural Illumination Microscopy (3D-SIM)

The glycocalyx of live PC12 cells in the indicated experimental conditions (prepared as described in 4.4) was marked 30 min before the recording by adding Oregon Green™ 488 conjugate wheat germ agglutinin (WGA, Thermofisher) to the medium at a final concentration of 25 µM/mL. WGA binds sialic acid and N-acetylglucosaminyl residues. After the 30 min incubation (in the incubator at 37 °C and 5% CO<sub>2</sub>), the cells were washed 3 × with PBS to remove the excess of WGA (to reduce the background fluorescence noise) and new phenol red-free medium (prewarmed to 37 °C) was given to the cells (in case of glycocalyx-targeting enzymatic treatment containing again the enzymes). Then the plates were immediately transferred to the 3D-SIM Nikon A1 microscope (equipped with a stage-top incubation system (Okolab), conditions: humid, 37 °C, 5% CO<sub>2</sub>) to take the images. An oil immersion 63 × objective was used.

The thickness of the glycocalyx was determined from crops of the cell borders in the plane just above the cell/substrate interaction zone processed by means of ImageJ/FIJI [109] (for better distinction the “Enhance Contrast” tool was applied). The thickness measurements from the cropped images were then done with a customised



macro in the MatLab environment that automatized the data collection after marking the thickness with lines. Filopodia were excluded from the measurement, as it was difficult to clearly distinguish the glycocalyx/cytosol boundary of the filopodia, because the filopodial tubular structures are very thin (see the representative example in Fig. 2E).

### Visualisation, recording and quantification of the actin dynamics

#### *Transfection with LifeAct<sup>TM</sup> and recording*

To visualise the actin dynamics, the PC12 cells were transfected with mCherry-LifeAct (the vector was a kind gift by Prof. Giorgio Scita). For this purpose, the cells were plated on Ø 35 mm petri dishes (TRP) at a low confluency (10–15%) the day before the transfection. At the beginning of the next day, the transfection was done with Lipofectamine LTX<sup>®</sup> performing the following steps:

- Solution 1: 6 µl of Lipofectamine LTX<sup>®</sup> was added to 150 µl RPMI base medium (incubation for 5 min at RT)
- Solution 2: 2 µl of the mCherry-LifeAct vector DNA (concentration 1 µg/µL) was added to 150 µl RPMI base medium, then 2 µl Plus<sup>TM</sup> reagent was added
- The two solutions were mixed and incubated for 20 min at RT and then added dropwise to the cells in a homogeneous way.

The success of the transfection was controlled the next day with a Zeiss Axiovert 40 CFL with an epifluorescence module.

After transferring the transfected cells onto the indicated substrates (see 4.4), the actin dynamics (before and after glycocalyx removal, see 4.4) were then recorded the next day with a Nikon A1R confocal microscope at the UNI<sup>TECH</sup> NOLIMITS Imaging facility of the University of Milan. The microscope is equipped with a stage-top incubation system (Okolab) to guarantee humidification, 37 °C and 5% CO<sub>2</sub> during the live cell imaging. An oil immersion 60 × objective was used. The recordings were done with a frame rate of 0.5 frames/sec for 2 min.

#### *Analysis of the actin dynamics by Particle Image Velocimetry*

Particle image velocimetry (PIV) was performed to quantify the actin dynamics. This analysis results in a vector field, highlighting the local movement of the actin fibres in time, from which the average flow speed can be obtained.

*Pre-processing* Photobleaching was corrected in Fiji [109] hypothesising linear decay of the signal and the cell

area was segmented by thresholding. A temporal resolution of 6 s between frames was used (intermediate frames were removed).

*Analysis* PIV analysis is described in detail elsewhere [110]. Briefly, a region of interest (source box) is searched for in a larger area (search box) of the subsequent frame by two-dimensional cross-correlation. A grid of regions of interest is drawn over the image, to obtain a full local tracking of the actin filaments. For this analysis, the PIV parameters were optimised as follows: source box 0.6 µm, search box 1 µm, distance between regions of interests (grid) 0.4 µm, correlation coefficient threshold of 0.3. Spatial and temporal convolutions are subsequently performed to interpolate the vector field. The defined kernels were 5 µm (sigma = 1 µm) and 30 s (sigma = 12 s), respectively. Colour maps display flow velocity within a 0–2 µm/min scale.

### Supplementary Information

The online version contains supplementary material available at <https://doi.org/10.1186/s12951-022-01585-5>.

**Additional file 1.** The retrograde actin flow videos should also be mentioned here.

**Additional file 2.** The retrograde actin flow videos should also be mentioned here.

**Additional file 3.** The retrograde actin flow videos should also be mentioned here.

**Additional file 4.** The retrograde actin flow videos should also be mentioned here.

**Additional file 5.** The retrograde actin flow videos should also be mentioned here.

### Acknowledgements

We thank the UNI<sup>TECH</sup> NOLIMITS Imaging facility of the University of Milan (in particular Dr. Miriam Ascagni) for support in regard to the realisation of the experiments involving confocal microscopy and 3D-SIM.

We thank Prof. Giorgio Scita, Prof. Jan de Boer, Prof. Johanna Ivaska, Dr. Martina Lerche and Aleksis Isomursu for critical reading of the drafts and valuable comments.

### Author contributions

Conceptualisation: MC, AP, CS; methodology – probe fabrication and characterisation: MC, AP, FB, CP; methodology – SCBD: AP, CP; methodology – modelling: MC, FB, CS, AP; methodology – cell culture and preparation: TD, MDU, CS; methodology – glycocalyx characterisation AFM: MC, LC, TD, CS, AP; methodology – AFM adhesion force spectroscopy: MC, TD, AP; methodology – actin dynamics: MDU, CS; methodology – glycocalyx characterisation 3D-SIM: MDU, CS; data curation and formal analysis – modelling: MC, FB, AP; data curation and formal analysis – AFM glycocalyx characterisation: MC, LC, TD, CS, AP; data curation and formal analysis – AFM adhesion force spectroscopy: MC, TD, CS, AP; data curation and formal analysis – actin dynamics: MDU, SM, BS, CS; data curation and formal analysis—glycocalyx characterisation 3D-SIM: CF, CS; original draft writing: MC, CS; draft reviewing and editing: MC, TD, FB, CL, PM, SM, BS, AP, CS; supervision: CL, PM, BS, CS, AP; resources, funding and project administration: CL, PM, BS, AP. Author contributions were allocated adopting the terminology of CRediT – Contributor Roles Taxonomy. All authors read and approved the final manuscript.

### Funding

We acknowledge the support of the European Union's Horizon 2020 research and innovation programme under the Marie Skłodowska-Curie grant agreement No. 812772, project Phys2Biomed, and under FET Open grant agreement No. 801126, project EDIT. BS and SM are funded by the European Research Council (ERC) under the European Union's Horizon 2020 research and innovation programme (grant agreement No. 681808). PM and CS acknowledge support from the European Union FP7-NMP-2013-LARGE-7 "Future NanoNeeds" programme. CL gratefully acknowledges funding from Miur – PRIN2017, Prot. 2017YH9MRK.

### Availability of data and materials

The data in this work are available in the manuscript, the Additional file, or from the corresponding authors upon reasonable request.

### Declarations

#### Ethics approval and consent to participate

Not applicable.

#### Consent for publication

All authors consent to the publication of the manuscript.

#### Competing interests

The authors declare that there is no conflict of interest.

#### Author details

<sup>1</sup>Interdisciplinary Centre for Nanostructured Materials and Interfaces (C.I.Ma.I.Na.) and Department of Physics "Aldo Pontremoli", University of Milan, Milan, Italy. <sup>2</sup>The FIRC Institute of Molecular Oncology (IFOM), Milan, Italy. <sup>3</sup>Randall Centre for Cell and Molecular Biophysics, King's College London, London, UK. <sup>4</sup>Department of Biomedical Engineering, Institute for Complex Molecular Systems, Eindhoven University of Technology, Eindhoven, Netherlands.

Received: 5 May 2022 Accepted: 29 July 2022

Published online: 19 September 2022

### References

- Gauthier NC, Roca-Cusachs P. Mechanosensing at integrin-mediated cell–matrix adhesions: from molecular to integrated mechanisms. *Curr Opin Cell Biol.* 2018;50:20–6.
- Kechagia JZ, Ivaska J, Roca-Cusachs P. Integrins as biomechanical sensors of the microenvironment. *Nat Rev Mol Cell Biol.* 2019. <https://doi.org/10.1038/s41580-019-0134-2>.
- Jansen KA, et al. A guide to mechanobiology: where biology and physics meet. *Mol Cell Res.* 2015;1853:3043–52.
- Di Cio S, Gautrot JE. Cell sensing of physical properties at the nanoscale: mechanisms and control of cell adhesion and phenotype. *Acta Biomater.* 2016;30:26–48.
- Sun Z, Costell M, Fässler R. Integrin activation by talin, kindlin and mechanical forces. *Nat Cell Biol.* 2019;21:25.
- Chighizola M, et al. Mechanotransduction in neuronal cell development and functioning. *Biophys Rev.* 2019. <https://doi.org/10.1007/s12551-019-00587-2>.
- Dalby MJ, Gadegaard N, Oreffo ROC. Harnessing nanotopography and integrin-matrix interactions to influence stem cell fate. *Nat Mater.* 2014;13:558–69.
- Chen W, Shao Y, Li X, Zhao G, Fu J. Nanotopographical surfaces for stem cell fate control: engineering mechanobiology from the bottom. *Nano Today.* 2014;9:759–84.
- Schulte C, et al. Conversion of nanoscale topographical information of cluster-assembled zirconia surfaces into mechanotransductive events promotes neuronal differentiation. *J Nanobiotechnol.* 2016;14:18.
- Maffioli E, et al. Proteomic dissection of nanotopography-sensitive mechanotransductive signalling hubs that foster neuronal differentiation in PC12 cells. *Front Cell Neurosci.* 2017. <https://doi.org/10.3389/fncel.2017.00417>.
- Chen W, et al. Nanotopography regulates motor neuron differentiation of human pluripotent stem cells. *Nanoscale.* 2018. <https://doi.org/10.1039/C7NR05430K>.
- Baek J, et al. Distinct mechanosensing of human neural stem cells on extremely limited anisotropic cellular contact. *ACS Appl Mater Interfaces.* 2018. <https://doi.org/10.1021/acsami.8b10171>.
- Galli A, et al. Cluster-assembled zirconia substrates promote long-term differentiation and functioning of human islets of Langerhans. *Sci Rep.* 2018;8:9979.
- Park J, et al. Directed migration of cancer cells guided by the graded texture of the underlying matrix. *Nat Mater.* 2016;15:792–801.
- Park J, Kim D-H, Levchenko A. Topotaxis: a new mechanism of directed cell migration in topographic ECM gradients. *Biophys J.* 2018;114:1257–63.
- Chighizola M, et al. Adhesion force spectroscopy with nanostructured colloidal probes reveals nanotopography-dependent early mechanotransductive interactions at the cell membrane level. *Nanoscale.* 2020. <https://doi.org/10.1039/D0NR01991G>.
- Boettiger D, Wehrle-Haller B. Integrin and glycocalyx mediated contributions to cell adhesion identified by single cell force spectroscopy. *J Phys Condens Matter.* 2010;22: 194101.
- Paszek MJ, et al. The cancer glycocalyx mechanically primes integrin-mediated growth and survival. *Nature.* 2014;511:319–25.
- Sun Z, Guo SS, Fässler R. Integrin-mediated mechanotransduction. *J Cell Biol Jcb.* 2016. <https://doi.org/10.1083/jcb.201609037>.
- Xu G-K, Qian J, Hu J. The glycocalyx promotes cooperative binding and clustering of adhesion receptors. *Soft Matter.* 2016;12:4572–83.
- Kuo JC-H, Gandhi JG, Zia RN, Paszek MJ. Physical biology of the cancer cell glycocalyx. *Nat Phys.* 2018;14:658–69.
- Marsico G, Russo L, Quondamatteo F, Pandit A. Glycosylation and integrin regulation in cancer. *Trends Cancer.* 2018;4:537–52.
- Shurer CR, et al. Physical principles of membrane shape regulation by the glycocalyx. *Cell.* 2019;177:1757–1770.e21.
- Buffone A, Weaver VM. Don't sugarcoat it: how glycocalyx composition influences cancer progression. *J Cell Biol.* 2020. <https://doi.org/10.1083/jcb.201910070>.
- Kanyo N, et al. Glycocalyx regulates the strength and kinetics of cancer cell adhesion revealed by biophysical models based on high resolution label-free optical data. *Sci Rep.* 2020;10:22422.
- Wegner K, Piseri P, Tafreshi HV, Milani P. Cluster beam deposition: a tool for nanoscale science and technology. *J Phys D: Appl Phys.* 2006;39:R439.
- Schulte C, Podestà A, Lenardi C, Tedeschi G, Milani P. Quantitative control of protein and cell interaction with nanostructured surfaces by cluster assembling. *Acc Chem Res.* 2017;50:231–9.
- Gasiorowski JZ, Murphy CJ, Nealey PF. Biophysical cues and cell behavior: the big impact of little things. *Annu Rev Biomed Eng.* 2013;15:155–76.
- Leclech C, Natale CF, Barakat AI. The basement membrane as a structured surface—role in vascular health and disease. *J Cell Sci.* 2020. <https://doi.org/10.1242/jcs.239889>.
- Schulte C, et al. Scale invariant disordered nanotopography promotes hippocampal neuron development and maturation with involvement of mechanotransductive pathways. *Front Cell Neurosci.* 2016;10:267.
- Alessandra G, et al. Shaping pancreatic  $\beta$ -cell differentiation and functioning: the influence of mechanotransduction. *Cells.* 2020;9:413.
- Schulte C. Cluster-assembled nanostructured materials for cell biology. In: Milani P, Sowwan M, editors. *Frontiers of Nanoscience.* Amsterdam: Elsevier; 2020.
- Maffioli E, et al. Proteomic analysis reveals a mitochondrial remodeling of  $\beta$ tc3 cells in response to nanotopography. *Front Cell Dev Biol.* 2020. <https://doi.org/10.3389/fcell.2020.00508>.
- Sokolov I, Iyer S, Subba-Rao V, Gaikwad RM, Woodworth CD. Detection of surface brush on biological cells in vitro with atomic force microscopy. *Appl Phys Lett.* 2007;91: 023902.
- Iyer S, Gaikwad RM, Subba-Rao V, Woodworth CD, Sokolov I. AFM detects differences in the surface brush of normal and cancerous cervical cells. *Nat Nanotechnol.* 2009;4:389–93.

36. Sokolov I, Dokukin ME, Guz NV. Method for quantitative measurements of the elastic modulus of biological cells in AFM indentation experiments. *Methods*. 2013;60:202–13.
37. Dokukin M, et al. Pericellular brush and mechanics of guinea pig fibroblast cells studied with AFM. *Biophys J*. 2016;111:236–46.
38. Kirfel G, Rigort A, Borm B, Schulte C, Herzog V. Structural and compositional analysis of the keratinocyte migration track. *Cell Motil*. 2003;55:1–13.
39. Kirfel G, Rigort A, Borm B, Herzog V. Cell migration: mechanisms of rear detachment and the formation of migration tracks. *Eur J Cell Biol*. 2004;83:717–24.
40. Ma L, et al. Discovery of the migrasome, an organelle mediating release of cytoplasmic contents during cell migration. *Cell Res*. 2015;25:24–38.
41. Paszek MJ, Boettiger D, Weaver VM, Hammer DA. Integrin clustering is driven by mechanical resistance from the glycocalyx and the substrate. *PLoS Comput Biol*. 2009;5: e1000604.
42. Arnold M, et al. Activation of integrin function by nanopatterned adhesive interfaces. *ChemPhysChem*. 2004;5:383–8.
43. Cavalcanti-Adam EA, et al. Cell spreading and focal adhesion dynamics are regulated by spacing of integrin ligands. *Biophys J*. 2007;92:2964–74.
44. Liu Y, et al. Nanoparticle tension probes patterned at the nanoscale: impact of integrin clustering on force transmission. *Nano Lett*. 2014;14:5539–46.
45. Changede R, Cai H, Wind SJ, Sheetz MP. Integrin nanoclusters can bridge thin matrix fibres to form cell–matrix adhesions. *Nat Mater*. 2019. <https://doi.org/10.1038/s41563-019-0460-y>.
46. Schwartzman M, et al. Nanolithographic control of the spatial organization of cellular adhesion receptors at the single-molecule level. *Nano Lett*. 2011;11:1306–12.
47. Coyer SR, et al. Nanopatterning reveals an ECM area threshold for focal adhesion assembly and force transmission that is regulated by integrin activation and cytoskeleton tension. *J Cell Sci*. 2012;125:5110–23.
48. Malmström J, et al. Large area protein patterning reveals nanoscale control of focal adhesion development. *Nano Lett*. 2010;10:686–94.
49. Huang J, et al. Impact of order and disorder in RGD nanopatterns on cell adhesion. *Nano Lett*. 2009;9:1111–6.
50. Vicente-Manzanares M, Horwitz AR. Adhesion dynamics at a glance. *J Cell Sci*. 2011;124:3923–7.
51. Changede R, Sheetz M. Integrin and cadherin clusters: a robust way to organize adhesions for cell mechanics. *BioEssays*. 2017;39:e201600123.
52. Li F, Redick SD, Erickson HP, Moy VT. Force measurements of the alpha-5beta1 integrin-fibronectin interaction. *Biophys J*. 2003;84:1252–62.
53. Taubenberger A, et al. Revealing early steps of alpha2beta1 integrin-mediated adhesion to collagen type I by using single-cell force spectroscopy. *Mol Biol Cell*. 2007;18:1634–44.
54. Dufrêne YF, et al. Five challenges to bringing single-molecule force spectroscopy into living cells. *Nat Methods*. 2011;8:123–7.
55. Strohmeier N, Bharadwaj M, Costell M, Fässler R, Müller DJ. Fibronectin-bound alpha5beta1 integrins sense load and signal to reinforce adhesion in less than a second. *Nat Mater*. 2017;16:1262–70.
56. Evans EA, Calderwood DA. Forces and bond dynamics in cell adhesion. *Science*. 2007;316:1148–53.
57. Mescola A, et al. Probing cytoskeleton organisation of neuroblastoma cells with single-cell force spectroscopy. *J Mol Recognit*. 2012;25:270–7.
58. Elosegui-Artola A, et al. Mechanical regulation of a molecular clutch defines force transmission and transduction in response to matrix rigidity. *Nat Cell Biol*. 2016;18:540–8.
59. Oria R, et al. Force loading explains spatial sensing of ligands by cells. *Nature*. 2017;552:219.
60. Case LB, Waterman CM. Integration of actin dynamics and cell adhesion by a three-dimensional, mechanosensitive molecular clutch. *Nat Cell Biol*. 2015;17:955–63.
61. Gardel ML, et al. Traction stress in focal adhesions correlates biphasically with actin retrograde flow speed. *J Cell Biol*. 2008;183:999–1005.
62. Alexandrova AY, et al. Comparative dynamics of retrograde actin flow and focal adhesions: formation of nascent adhesions triggers transition from fast to slow flow. *PLoS One*. 2008;3:e3234.
63. Renkawitz J, et al. Adaptive force transmission in amoeboid cell migration. *Nat Cell Biol*. 2009;11:1438–43.
64. Schulte C, et al. Lamellipodial tension, not integrin/ligand binding, is the crucial factor to realise integrin activation and cell migration. *Eur J Cell Biol*. 2016;95:1–14.
65. Nichol RH, Hagen KM, Lumbard DC, Dent EW, Gómez TM. Guidance of axons by local coupling of retrograde flow to point contact adhesions. *J Neurosci*. 2016;36:2267–82.
66. Stricker J, Aratyn-Schaus Y, Oakes PW, Gardel ML. Spatiotemporal constraints on the force-dependent growth of focal adhesions. *Biophys J*. 2011;100:2883–93.
67. Choi CK, et al. Actin and alpha-actinin orchestrate the assembly and maturation of nascent adhesions in a myosin II motor-independent manner. *Nat Cell Biol*. 2008;10:1039–50.
68. Di Cio S, Iskratsch T, Connolly JT, Gautrot JE. Contractile myosin rings and cofilin-mediated actin disassembly orchestrate ECM nanotopography sensing. *Biomaterials*. 2020;232: 119683.
69. Wolfenson H, et al. Tropomyosin controls sarcomere-like contractions for rigidity sensing and suppressing growth on soft matrices. *Nat Cell Biol*. 2016;18:33–42.
70. Sheetz M. A tale of two states: normal and transformed, with and without rigidity sensing. *Annu Rev Cell Dev Biol*. 2019;35:169–90.
71. Feld L, et al. Cellular contractile forces are nonmechanosensitive. *Sci Adv*. 2020;6:6997.
72. Changede R, Xu X, Margadant F, Sheetz MP. Nascent integrin adhesions form on all matrix rigidities after integrin activation. *Dev Cell*. 2015;35:614–21.
73. Chaudhuri PK, Low BC, Lim CT. Mechanobiology of tumor growth. *Chem Rev*. 2018;118:6499–515.
74. Lee G, Han S-B, Lee J-H, Kim H-W, Kim D-H. Cancer mechanobiology: microenvironmental sensing and metastasis. *ACS Biomater Sci Eng*. 2019. <https://doi.org/10.1021/acsbomaterials.8b01230>.
75. Yang B, et al. Stopping transformed cancer cell growth by rigidity sensing. *Nat Mater*. 2020;19:239–50.
76. Ingber D. Mechanobiology and diseases of mechanotransduction. *Ann Med*. 2003;35:564–77.
77. Hamidi H, Ivaska J. Every step of the way: integrins in cancer progression and metastasis. *Nat Rev Cancer*. 2018;18:533–48.
78. Pappalazarou V, Salmeron-Sanchez M, Machesky LM. Tissue engineering the cancer microenvironment—challenges and opportunities. *Biophys Rev*. 2018;10:1695–711.
79. Nebuloni M, et al. Insight On Colorectal Carcinoma Infiltration by Studying Perilesional Extracellular Matrix. *Sci Rep*. 2016;6:22522.
80. Bonnans C, Chou J, Werb Z. Remodelling the extracellular matrix in development and disease. *Nat Rev Mol Cell Biol*. 2014;15:786–801.
81. Cox TR. The matrix in cancer. *Nat Rev Cancer*. 2021. <https://doi.org/10.1038/s41568-020-00329-7>.
82. Tarbell JM, Cancel LM. The glycocalyx and its significance in human medicine. *J Intern Med*. 2016;280:97–113.
83. Winograd-Katz SE, Fässler R, Geiger B, Legate KR. The integrin adhesome: from genes and proteins to human disease. *Nat Rev Mol Cell Biol*. 2014;15:273–88.
84. Wolfenson H, Yang B, Sheetz MP. Steps in mechanotransduction pathways that control cell morphology. *Annu Rev Physiol*. 2019;81:585–605.
85. Barnes JM, et al. A tension-mediated glycocalyx–integrin feedback loop promotes mesenchymal-like glioblastoma. *Nat Cell Biol*. 2018;20:1203.
86. Chronopoulos A, et al. Syndecan-4 tunes cell mechanics by activating the kindlin-integrin-RhoA pathway. *Nat Mater*. 2020;19:669–78.
87. Freeman SA, et al. Transmembrane pickets connect Cyto- and pericellular skeletons forming barriers to receptor engagement. *Cell*. 2018;172:305–317. e10.
88. Ferraris GMS, et al. The interaction between uPAR and vitronectin triggers ligand-independent adhesion signalling by integrins. *EMBO J*. 2014;33:2458–72.
89. Miyata S, Kitagawa H. Formation and remodeling of the brain extracellular matrix in neural plasticity: roles of chondroitin sulfate and hyaluronan. *General Subjects*. 2017;1861:2420–34.
90. Lou H-Y, et al. Membrane curvature underlies actin reorganization in response to nanoscale surface topography. *PNAS*. 2019;116:23143–51.
91. Sheridan C. Pancreatic cancer provides testbed for first mechanotherapeutics. *Nat Biotechnol*. 2019;37:829–31.
92. Cully M. Integrin-targeted therapies branch out. *Nat Rev Drug Discovery*. 2020. <https://doi.org/10.1038/d41573-020-00180-3>.

93. Indrieri M, Podestà A, Bongiorno G, Marchesi D, Milani P. Adhesive-free colloidal probes for nanoscale force measurements: production and characterization. *Rev Sci Instrum.* 2011;82: 023708.
94. Chighizola M, Puricelli L, Bellon L, Podestà A. Large colloidal probes for atomic force microscopy: FABRICATION and calibration issues. *J Mol Recognit.* 2021;34: e2879.
95. Hutter JL, Bechhoefer J. Calibration of atomic-force microscope tips. *Rev Sci Instrum.* 1993;64:1868–73.
96. Butt H-J, Jaschke M. Calculation of thermal noise in atomic force microscopy. *Nanotechnology.* 1995;6:1.
97. Laurent J, Steinberger A, Bellon L. Functionalized AFM probes for force spectroscopy: eigenmode shapes and stiffness calibration through thermal noise measurements. *Nanotechnology.* 2013;24: 225504.
98. Barborini E, Piseri P, Milani P. A pulsed microplasma source of high intensity supersonic carbon cluster beams. *J Phys D: Appl Phys.* 1999;32:L105–9.
99. Tafreshi HV, Piseri P, Benedek G, Milani P. The role of gas dynamics in operation conditions of a Pulsed Microplasma Cluster Source for nanostructured thin films deposition. *J Nanosci Nanotechnol.* 2006;6:1140–9.
100. Podestà A, et al. Nanomanufacturing of titania interfaces with controlled structural and functional properties by supersonic cluster beam deposition. *J Appl Phys.* 2015;118: 234309.
101. Borghi F, Podestà A, Piazzoni C, Milani P. Growth mechanism of cluster-assembled surfaces: from submonolayer to thin-film regime. *Phys Rev Applied.* 2018;9: 044016.
102. Borghi F, et al. Cluster-assembled cubic zirconia films with tunable and stable nanoscale morphology against thermal annealing. *J Appl Phys.* 2016;120: 055302.
103. Borghi F, Scaparra B, Paternoster C, Milani P, Podestà A. Electrostatic double-layer interaction at the surface of rough cluster-assembled films: the case of nanostructured zirconia. *Langmuir.* 2018;34:10230–42.
104. Schillers H, et al. Standardized Nanomechanical Atomic Force Microscopy Procedure (SNAP) for measuring soft and biological samples. *Sci Rep.* 2017;7:5117.
105. Zeng Y, Ebong EE, Fu BM, Tarbell JM. The structural stability of the endothelial glycocalyx after enzymatic removal of glycosaminoglycans. *PLoS ONE.* 2012;7: e43168.
106. Janovjak H, Struckmeier J, Müller DJ. Hydrodynamic effects in fast AFM single-molecule force measurements. *Eur Biophys J.* 2005;34:91–6.
107. Puricelli L, Galluzzi M, Schulte C, Podestà A, Milani P. Nanomechanical and topographical imaging of living cells by atomic force microscopy with colloidal probes. *Rev Sci Instrum.* 2015;86: 033705.
108. Wiesinger A, et al. Nanomechanics of the endothelial glycocalyx in experimental sepsis. *PLoS ONE.* 2013;8: e80905.
109. Schindelin J, et al. Fiji: an open-source platform for biological-image analysis. *Nat Methods.* 2012;9:676–82.
110. Yolland L, et al. Persistent and polarized global actin flow is essential for directionality during cell migration. *Nat Cell Biol.* 2019;21:1370–81.

## Publisher's Note

Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

Ready to submit your research? Choose BMC and benefit from:

- fast, convenient online submission
- thorough peer review by experienced researchers in your field
- rapid publication on acceptance
- support for research data, including large and complex data types
- gold Open Access which fosters wider collaboration and increased citations
- maximum visibility for your research: over 100M website views per year

At BMC, research is always in progress.

Learn more [biomedcentral.com/submissions](https://biomedcentral.com/submissions)



# SUPPLEMENTARY INFORMATION

## The glycolyx affects the mechanotransductive perception of topographical microenvironment

<sup>1</sup>Matteo Chighizola<sup>F</sup>, <sup>1,2</sup>Tania Dini, <sup>3</sup>Stefania Marcotti, <sup>1,4</sup>Mirko D'Urso, <sup>1</sup>Claudio Piazzoni, <sup>1</sup>Francesca Borghi, <sup>1</sup>Anita Previdi, <sup>1</sup>Laura Ceriani, <sup>1</sup>Claudia Folliero, <sup>3</sup>Brian Stramer, <sup>1</sup>Cristina Lenardi, <sup>1</sup>Paolo Milani, <sup>1</sup>Alessandro Podestà\*, <sup>1</sup>Carsten Schulte\*

### **Affiliations:**

[matteo.chighizola@unimi.it](mailto:matteo.chighizola@unimi.it), [claudio.piazzoni@unimi.it](mailto:claudio.piazzoni@unimi.it), [francesca.borghi@unimi.it](mailto:francesca.borghi@unimi.it), [anita.previdi@unimi.it](mailto:anita.previdi@unimi.it),  
[laura.ceriani3@studenti.unimi.it](mailto:laura.ceriani3@studenti.unimi.it), [follieroclaudia@gmail.com](mailto:follieroclaudia@gmail.com), [cristina.lenardi@unimi.it](mailto:cristina.lenardi@unimi.it), [paolo.milani@mi.infn.it](mailto:paolo.milani@mi.infn.it),  
[alessandro.podesta@mi.infn.it](mailto:alessandro.podesta@mi.infn.it), [carsten.schulte@unimi.it](mailto:carsten.schulte@unimi.it)

<sup>1</sup>Interdisciplinary Centre for Nanostructured Materials and Interfaces (C.I.Ma.I.Na.) and Department of Physics "Aldo Pontremoli", University of Milan, Milan, Italy

[tania.dini@ifom.eu](mailto:tania.dini@ifom.eu)

<sup>2</sup>The FIRC Institute of Molecular Oncology (IFOM), Milan, Italy

[stefania.marcotti@kcl.ac.uk](mailto:stefania.marcotti@kcl.ac.uk), [brian.m.stramer@kcl.ac.uk](mailto:brian.m.stramer@kcl.ac.uk)

<sup>3</sup>Randall Centre for Cell and Molecular Biophysics, King's College London, London, United Kingdom

[m.d.urso@tue.nl](mailto:m.d.urso@tue.nl)

<sup>4</sup>Department of Biomedical Engineering, Institute for Complex Molecular Systems, Eindhoven University of Technology, Eindhoven, Netherlands

<sup>F</sup> first author

### **\*Co-last and corresponding authors:**

Carsten Schulte: [carsten.schulte@unimi.it](mailto:carsten.schulte@unimi.it)

Alessandro Podestà: [alessandro.podesta@mi.infn.it](mailto:alessandro.podesta@mi.infn.it)

### **Contents**

1. Implementation of the Sokolov's brush-Model .....	2
2. 3D-SIM Glycolyx imaging .....	5
3. Representation and analysis of the nanotopographical substrate features .....	6
4. Further parameters extracted from the adhesion force spectroscopy measurements – Work W and Number of tethers $N_t$ .....	7
5. Jump force data distribution .....	8

### **Keywords:**

Mechanotransduction, glycolyx, integrin adhesion complexes, molecular clutch, force loading, focal adhesion, nanostructured cell microenvironment, nanotopography, **adhesion force spectroscopy**, Atomic Force Microscopy, colloidal probes.

## 1. Implementation of the Sokolov's brush-Model

Following the approach described in Refs <sup>1,2,3</sup>, the cell and the glycocalyx can be thought of as a two-layer system with two different elastic properties. In the geometry of the indentation experiment the **probe-membrane** distance  $h$  can be described as:

$$h = Z - Z_0 + i + d \quad (1)$$


Where  $Z$  is the relative piezo position,  $Z_0$  is the undeformed position of the cellular membrane,  $d$  the deflection of the cantilever, which is positive when the cantilever is bent upward (in repulsive regime), and  $i$  the indentation calculated using the Hertz model

$$i = \left( \frac{3k(1-\nu^2)}{4E} R^{1/2} \right)^{2/3} d^{2/3} \quad (2)$$

Here  $E$  is the Young's modulus of the cell body,  $k$  is the spring constant of the probe,  $\nu=0.5$  is the Poisson coefficient.

Assuming that the glycocalyx layer is much softer than the cell body, the cantilever reaches an applied force where the glycocalyx can be considered completely squeezed ( $h=0$ ) before reaching the maximum load set. This assumption depends obviously on the value of the force threshold applied, which should be sufficiently large; in this condition  $(Z - Z_0) + d = -i$ , as in conventional indentation experiments.

The force needed to completely squeeze the glycocalyx cannot be known *a priori* and must be found. Our approach was to divide the total effective deformation  $\delta_{eff}$  (squeezing of the glycocalyx plus cellular deformation) in intervals  $s=200$  nm and then apply the hertz model in those intervals. The idea behind this approach (already used to detect the glycocalyx mechanical response<sup>4,5</sup>) is that the first mechanical response perceived by the probe would be the resistance to compression of the pericellular brush, then applying more and more force the glycocalyx will squeeze and progressively transfers rigidly the applied force to the cell below. Once the glycocalyx will be completely compressed the resulting effective Young's modulus  $E_{eff}$  will stabilise to the cell body-bulk values. The  $E_{eff}$  was plotted as function of the  $\delta_{eff}$  and then we looked at discontinuity in the  $E_{eff}$  and where it reaches a plateau. We interpreted the plateau as a situation where the glycocalyx is fully compressed and what is measured is the Young's modulus of the cell body. The result of this analysis was made on a population of ~20 cells in standard conditions (represented in **SI - Fig. S1**).

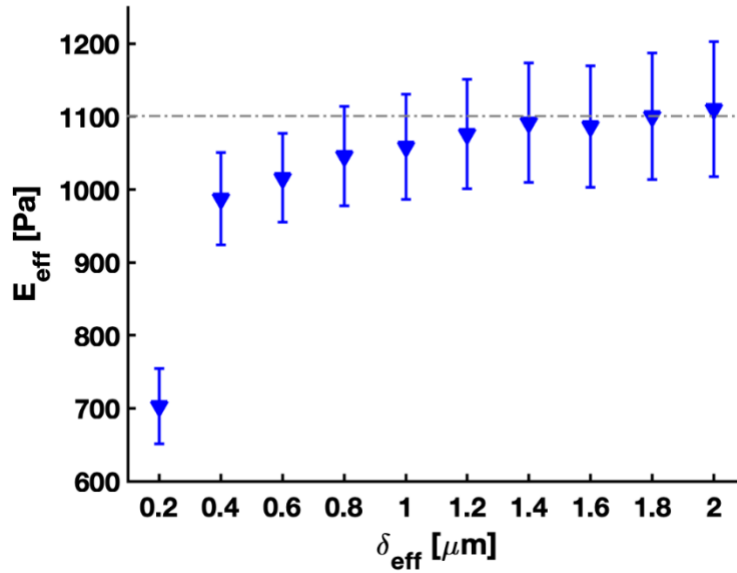


**SI – Fig. S1.** Effective YM  $E_{\text{eff}}$  evaluated per each intervals  $s$  as a function of the effective indentation  $d_{\text{eff}}$ . Data represent the mean YM averaged over the cell population, while the error bars represent the standard deviation.

It can be noted that after the first 200 nm a sudden increase of the  $E_{\text{eff}}$  is present. The subsequent smooth increase of  $E_{\text{eff}}$  can be attributed to inhomogeneity in the elastic properties of the cellular interior (e.g., cortex vs nucleus) and to finite-thickness effects<sup>6</sup>. The corresponding force threshold, at which the glycocalyx is fully compressed was set at  $F_{\text{thr}} = 0.1\text{-}0.2 \text{ nN}$ .

Fitting the hertz model in a region just above  $F_{\text{thr}}$  (where  $h \cong 0$ ) would provide a value of  $E$  in the superficial region. The intersection of a back extrapolation of the hertz model and the horizontal line ( $F=0$ ) would give the value of the parameter  $Z_0$ , that represents the contact point between the probe and the cell membrane. Using then Eq. 2, it is possible to evaluate the indentation  $i$  (which actually is the real deformation of the cell, beneath the glycocalyx compression). With all these parameters, it is possible to calculate the probe-membrane distance  $h$  at every position of the piezo.

Note that care must be taken in the choice of the indentation range for the fit of the Hertz model; as it is evident from **SI - Fig. S1** that the inner cell body is anything but uniform. The cell body is isotropic and this inhomogeneity is reflected by the change of the YM. When choosing a fitting region, one has to take into account that, looking at Eq. 1, the aim of the procedure is to quantify the cellular deformation within the effective indentation  $\delta_{\text{eff}}$ , in order to obtain the residual deflection of the probe, i.e. the effect only due to the brush steric resistance. Therefore, the YM should be extracted from the first indentation range above the threshold, identified in **SI - Fig. S1**, otherwise the probe-membrane distance and then the glycocalyx thickness would be estimated inaccurately.

Once the probe-membrane distance is evaluated the FCs must be rescaled on this new distance as shown in **SI - Fig. S2**.

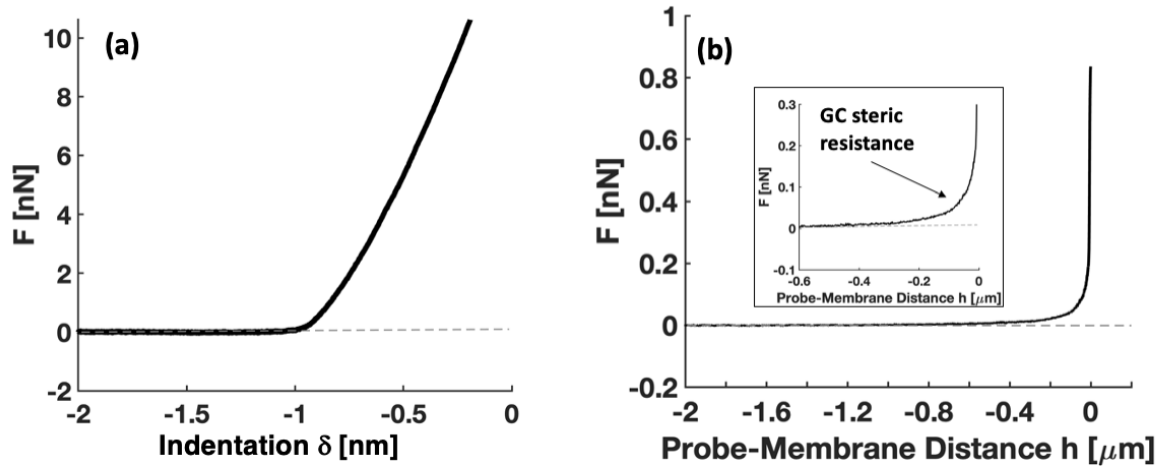

**SI – Fig. S2.** (a) Original Force Vs Indentation curve taken over the cell body. (b) Same curve rescaled over the new distance  $h$ . After the glycocalyx complete compression ( $F = 0.2$  nN), the probe is in contact with the membrane and the rest of the curve collapses on the  $h=0$  vertical axis. The inset shows the appearance of the glycocalyx' steric resistance a few hundred of nm before the probe gets into contact with the cell membrane.


Because of the specific force dependence and its physical nature (actually intertwined polymer chains) the glycocalyx layer cannot be described by an effective YM. The glycocalyx layer increases its stiffness during the compression. To describe the glycocalyx behaviour quantitatively, the Alexander-de Gennes model was used, implemented by Butt *et al.*<sup>7</sup>. It describes the steric interaction between a spherical indenter of radius  $R$  and a flat surface due to the existence of superficial *entropic brush*<sup>8</sup>:

$$F(h) = 50k_B T R N^{3/2} L e^{-2\pi \frac{h}{L}} \quad (3)$$

Where  $k_b$  is Boltzmann's constant,  $T$  is the medium temperature,  $R$  is the probe radius,  $N$  the brush grafting density and  $L$  the brush length-thickness. From the fitting of the force rescaled data with Eq (3), it is possible to extract the thickness parameters  $L$ .




## 2. 3D-SIM Glycocalyx imaging

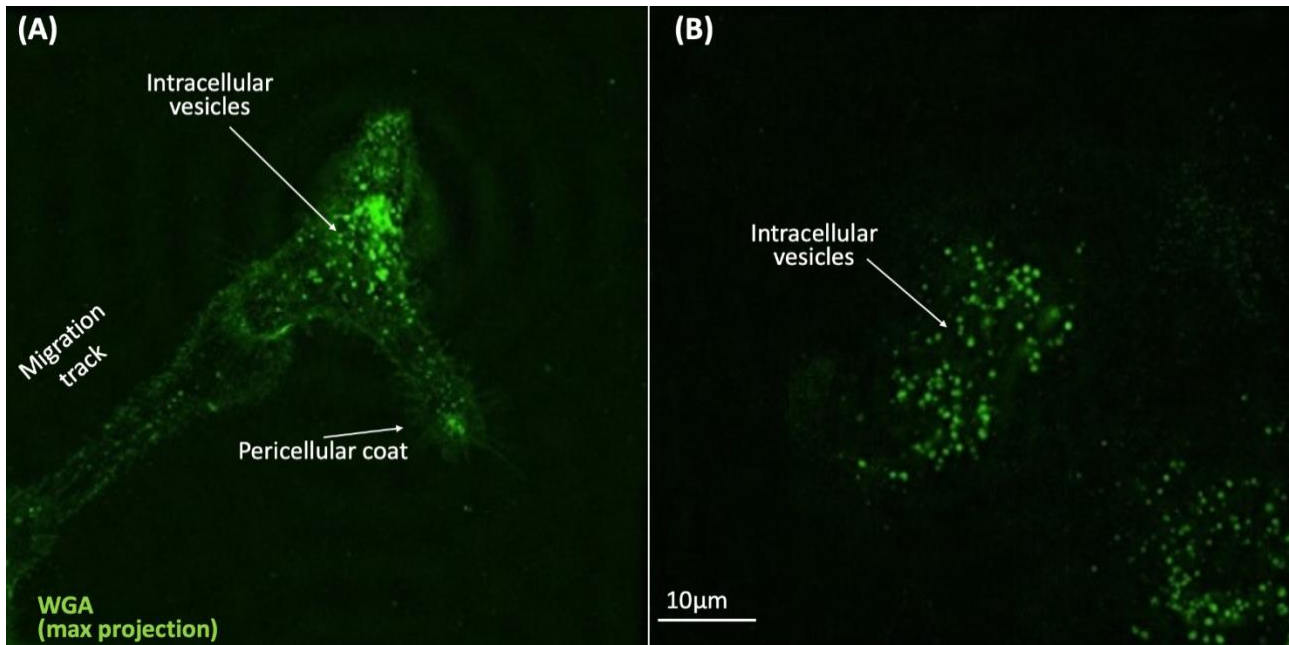


**SI – Fig. S3.** Representative 3D-SIM images (max. projection) of **(A)** PC12 on PLL, native or **(B)** treated with the glycocalyx-targeting cocktail, marked with Oregon Green<sup>®</sup>488 conjugated wheat germ agglutinin (WGA) which binds to sialic acid and N-acetylglucosaminyl residues.

The native PC12 cells show (**Fig. SI-S3A**) different glycocalyx containing (extra)cellular structures stained in green, *i.e.* intracellular vesicles filled with glycocalyx components, the pericellular glycocalyx coat and a migration track/migrasome (an extracellular structure/organelle known to be left behind some migrating cells<sup>9,10,11</sup>). After the enzymatic treatment (**Fig. SI-S3B**) all staining disappeared, except for the intracellular vesicles.

### 3. Representation and analysis of the nanotopographical substrate features

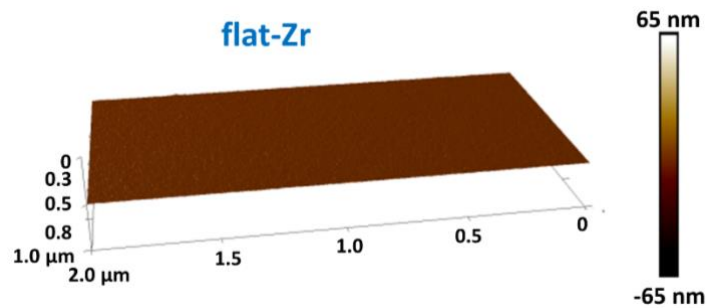


SI – Fig. S4) A representation of flat-Zr produced by Ion Gun sputtering.

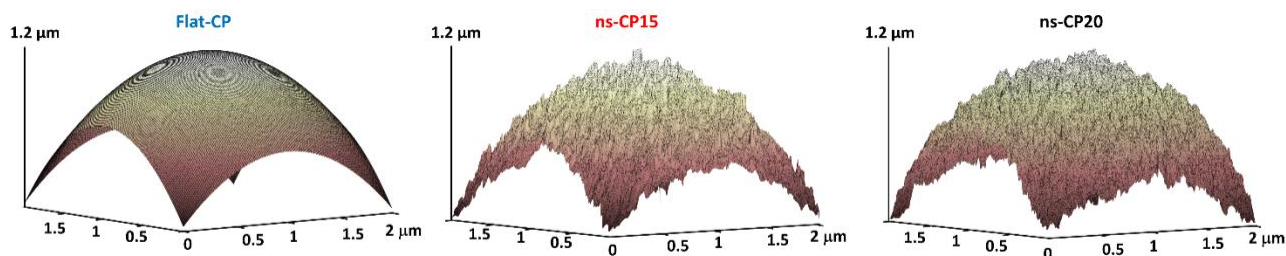

SI – Fig. S5) AFM scans of colloidal probes (CP) decorated with zirconium oxide ( $\text{ZrO}_x$ ). Left, CP with flat thin film of  $\text{ZrO}_x$  deposited with an ion gun. Middle and right, CPs decorated with nanostructured  $\text{ZrO}_x$  deposited by supersonic cluster beam deposition. Middle, CP with  $R_q = 15$  nm root-mean-square (rms). Right, CP with  $R_q = 20$  nm rms. The images were taken over probes with 5  $\mu\text{m}$  radius to appreciate both, the nanostructure and the sphere curvature.


4. Further parameters extracted from the adhesion force spectroscopy measurements –  
Work  $W$  and Number of tethers  $N_t$

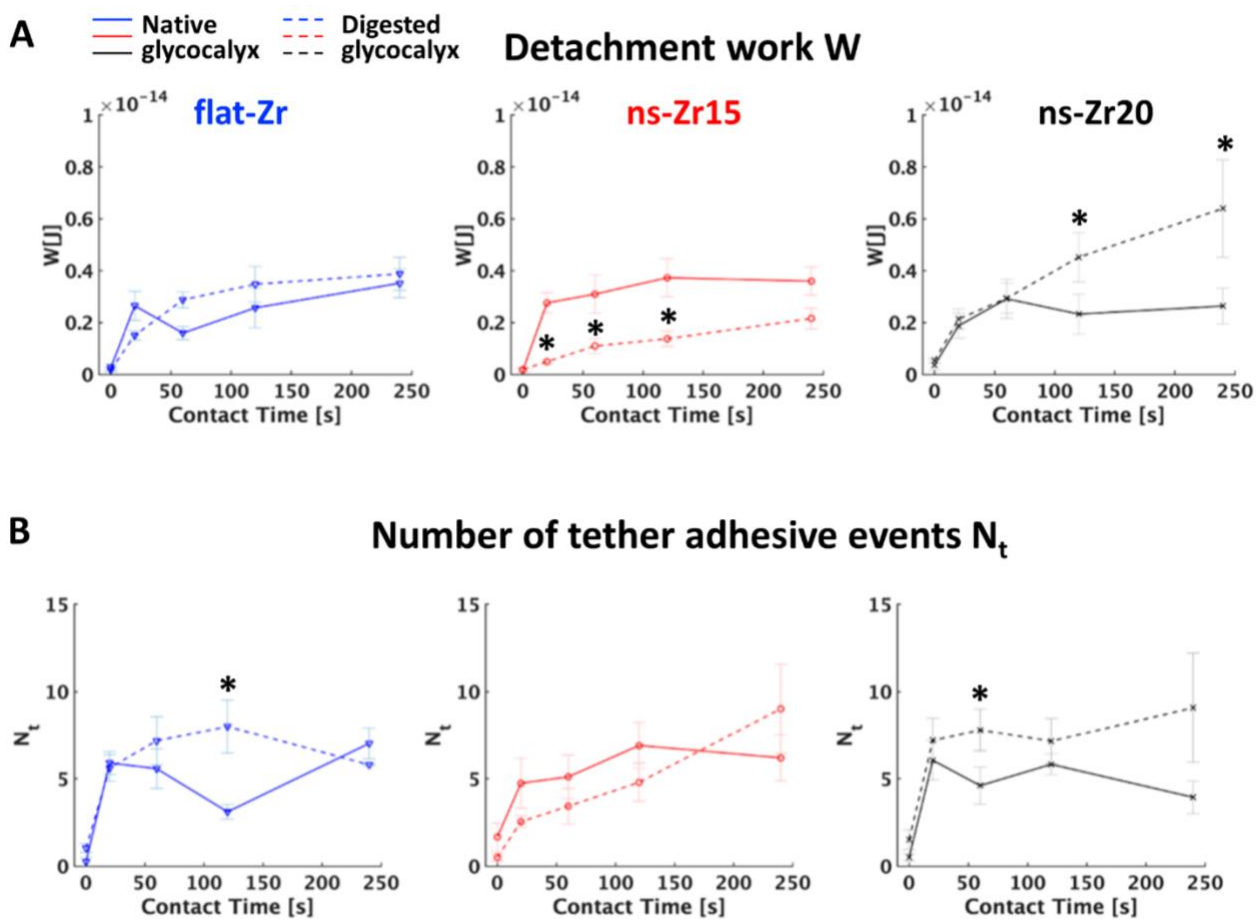

**SI – Fig. S6)** The panel shows the results of the adhesion force spectroscopy measurements for the different indicated experimental condition for the parameters **(A)** Detachment work  $W$  and **(B)** Number of tether adhesive events. Asterisks indicate a statistically significant difference between untreated and enzymatic treatment condition.

## 5. Jump force data distribution

### Jump force distribution

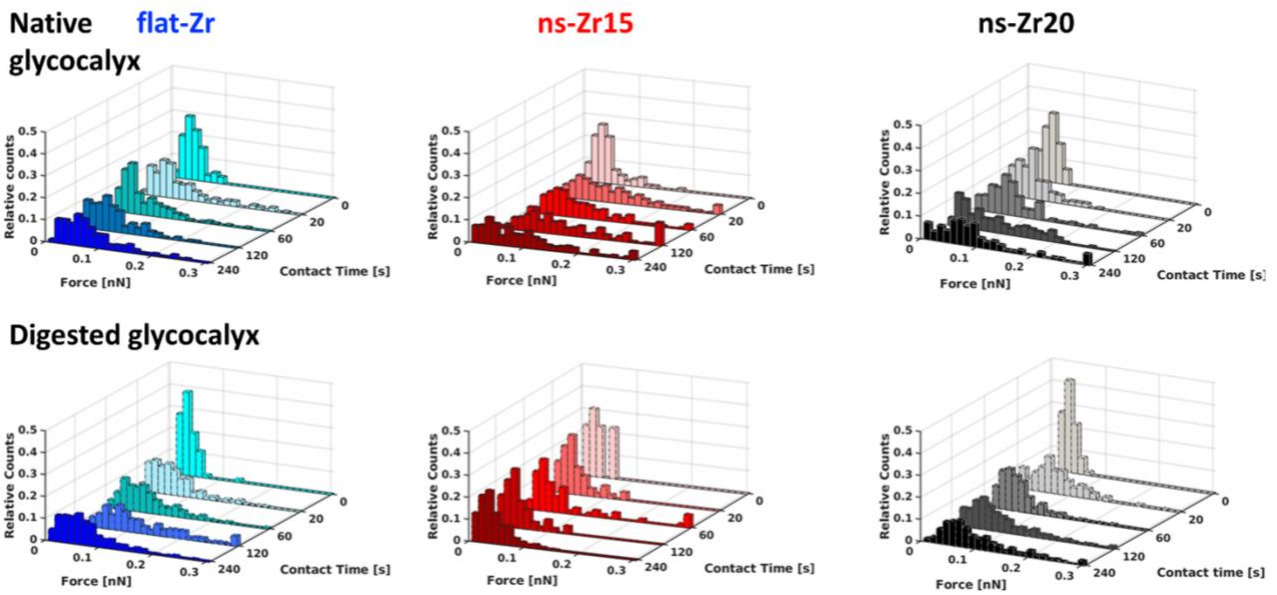

SI – Fig. S7) The panel shows the jump force distribution results in the indicated different experimental conditions of Fig. 3D in a finer binning to highlight the stronger dispersion of the higher forces in the untreated PC12 on ns-Zr15.

## References

1. Sokolov, I., Iyer, S., Subba-Rao, V., Gaikwad, R. M. & Woodworth, C. D. Detection of surface brush on biological cells in vitro with atomic force microscopy. *Appl. Phys. Lett.* **91**, 023902 (2007).
2. Simon, M. *et al.* Load Rate and Temperature Dependent Mechanical Properties of the Cortical Neuron and Its Pericellular Layer Measured by Atomic Force Microscopy. *Langmuir* **32**, 1111–1119 (2016).
3. Dokukin, M. *et al.* Pericellular Brush and Mechanics of Guinea Pig Fibroblast Cells Studied with AFM. *Biophys J* **111**, 236–246 (2016).
4. O’Callaghan, R., Job, K. M., Dull, R. O. & Hlady, V. Stiffness and heterogeneity of the pulmonary endothelial glycocalyx measured by atomic force microscopy. *American Journal of Physiology-Lung Cellular and Molecular Physiology* **301**, L353–L360 (2011).
5. Oberleithner, H. *et al.* Salt overload damages the glycocalyx sodium barrier of vascular endothelium. *Pflugers Arch - Eur J Physiol* **462**, 519 (2011).
6. Dimitriadis, E. K., Horkay, F., Maresca, J., Kachar, B. & Chadwick, R. S. Determination of Elastic Moduli of Thin Layers of Soft Material Using the Atomic Force Microscope. *Biophysical Journal* **82**, 2798–2810 (2002).
7. Butt, H.-J. *et al.* Steric Forces Measured with the Atomic Force Microscope at Various Temperatures. *Langmuir* **15**, 2559–2565 (1999).
8. *Surface and Interfacial Forces 2e.* (John Wiley & Sons, Ltd, 2018). doi:10.1002/9783527804351.
9. Kirfel, G., Rigort, A., Borm, B., Schulte, C. & Herzog, V. Structural and compositional analysis of the keratinocyte migration track. *Cell Motility* **55**, 1–13 (2003).
10. Kirfel, G., Rigort, A., Borm, B. & Herzog, V. Cell migration: mechanisms of rear detachment and the formation of migration tracks. *European Journal of Cell Biology* **83**, 717–724 (2004).
11. Ma, L. *et al.* Discovery of the migrasome, an organelle mediating release of cytoplasmic contents during cell migration. *Cell Res* **25**, 24–38 (2015).