

# Nonaffine lattice dynamics with the Ewald method reveals strongly nonaffine elasticity of $\alpha$ -quartz

Cite as: J. Chem. Phys. **151**, 224509 (2019); <https://doi.org/10.1063/1.5129025>

Submitted: 26 September 2019 . Accepted: 22 November 2019 . Published Online: 12 December 2019

Bingyu Cui, Alessio Zaccone, and David Rodney 



View Online



Export Citation



CrossMark

## ARTICLES YOU MAY BE INTERESTED IN

[Many-body effects at the origin of structural transitions in  \$B\_2O\_3\$](#)

The Journal of Chemical Physics **151**, 224508 (2019); <https://doi.org/10.1063/1.5131763>

[An efficient computational procedure to obtain a more stable glass structure](#)

The Journal of Chemical Physics **151**, 224502 (2019); <https://doi.org/10.1063/1.5133413>

[The dynamics of the plastically crystalline phase of cyanoadamantane revisited by NMR line shape analysis and field-cycling relaxometry](#)

The Journal of Chemical Physics **151**, 224507 (2019); <https://doi.org/10.1063/1.5126953>

Lock-in Amplifiers

Find out more today



 Zurich  
Instruments

# Nonaffine lattice dynamics with the Ewald method reveals strongly nonaffine elasticity of $\alpha$ -quartz

Cite as: J. Chem. Phys. 151, 224509 (2019); doi: 10.1063/1.5129025

Submitted: 26 September 2019 • Accepted: 22 November 2019 •

Published Online: 12 December 2019



View Online



Export Citation



CrossMark

Bingyu Cui,<sup>1</sup> Alessio Zaccone,<sup>1,2,3,a)</sup> and David Rodney<sup>4,b)</sup> 

## AFFILIATIONS

<sup>1</sup>Cavendish Laboratory, University of Cambridge, JJ Thomson Avenue, CB3 0HE Cambridge, United Kingdom

<sup>2</sup>Department of Physics “A. Pontremoli”, University of Milan, via Celoria 16, 20133 Milano, Italy

<sup>3</sup>Statistical Physics Group, Department of Chemical Engineering and Biotechnology, University of Cambridge, Philippa Fawcett Drive, CB3 0AS Cambridge, United Kingdom

<sup>4</sup>Institut Lumière Matière, UMR 5306 Université Lyon 1-CNRS, Université de Lyon, F-69622 Villeurbanne, France

<sup>a)</sup>Electronic mail: [az302@cam.ac.uk](mailto:az302@cam.ac.uk)

<sup>b)</sup>Electronic mail: [david.rodney@univ-lyon1.fr](mailto:david.rodney@univ-lyon1.fr)

## ABSTRACT

A lattice dynamical formalism based on nonaffine response theory is derived for noncentrosymmetric crystals, accounting for long-range interatomic interactions using the Ewald method. The framework takes equilibrated static configurations as input to compute the elastic constants in excellent agreement with both experimental data and calculations under strain. Besides this methodological improvement, which enables faster evaluation of elastic constants without the need of explicitly simulating the deformation process, the framework provides insights into the nonaffine contribution to the elastic constants of  $\alpha$ -quartz. It turns out that, due to the noncentrosymmetric lattice structure, the nonaffine (softening) correction to the elastic constants is very large, such that the overall elastic constants are at least 3–4 times smaller than the affine Born-Huang estimate.

Published under license by AIP Publishing. <https://doi.org/10.1063/1.5129025>

## I. INTRODUCTION

Lattice dynamics has been formulated through the pioneering work of Max Born and co-workers on the simplifying assumption that deformations are homogeneous, or in modern language, affine.<sup>1</sup> In practice, this implies that every atom is displaced under deformation by the macroscopic strain tensor operating on the original position vectors. This transformation defines the affine positions in the deformed lattice. Such a description assumes, however, that mechanical equilibrium is satisfied at the affine positions, which is certainly true for centrosymmetric lattices, where, owing to each atom being a local center of inversion symmetry, the forces transmitted by the neighbors are canceled out by symmetry at the affine positions.

The situation is different for disordered lattices such as glasses and for noncentrosymmetric crystals as well as near crystalline

defects such as grain boundaries. In such cases, the atoms are not centers of symmetry in their affine positions and therefore receive from their neighbors forces that sum up to a net force. The latter is released via an extra displacement, called nonaffine displacement or relaxation.

A well-known consequence is that, in atomistic calculations of elastic constants where a periodic cell is strained to compute its energy- or stress-strain curve, atomic positions must be relaxed, i.e., the cell energy must be minimized, each time the periodic vectors of the cell are strained (see, for instance, Ref. 2). The effect of nonaffinity has been investigated much more intensely in glasses than in crystals because it is generally expected that relaxations will be larger in glasses due to their inherent disorder than in ordered crystals.


Moreover, the physical origin of the nonaffine relaxations cannot be addressed by direct numerical simulations. For this purpose,

Lemaitre and Maloney<sup>3</sup> following the pioneering work of Lutsko<sup>4</sup> expressed analytically the elastic constants of systems interacting through short-ranged potentials. They showed that the elastic constants can be expressed as the sum of a positive Born term due to affine deformations and a negative (softening) correction due to the nonaffine relaxations.

Reformulating the equations of motion by explicitly requiring that the atoms move along nonaffine pathways of mechanical equilibrium leads to a framework known as the nonaffine response theory or nonaffine lattice dynamics. This framework has recently been applied to various systems and materials, from packings [where it recovers the  $\sim(z - 2d)$  jamming scaling, with  $z$  being the coordination number<sup>5</sup>] to polymers,<sup>6</sup> and to analyze dissipation in high-frequency oscillatory rheology.<sup>7</sup> The framework also provides quantitative predictions of dynamic viscoelastic moduli of coarse-grained (Kremer-Grest) glassy polymers.<sup>8</sup>

One limitation so far of this analytical approach has been that it can be applied only to short-ranged potentials, such as pair or embedded-atom method potentials with a cut-off radius and cannot handle long-ranged interactions. It cannot in particular handle Coulomb interactions. In fact in disordered glasses, long-ranged Coulomb interactions have been treated with a truncation<sup>9–11</sup> and were handled using the original approach of Lemaitre and Maloney.<sup>7</sup> By way of contrast, in an ordered crystal such as  $\alpha$ -quartz, Coulomb interactions are conditionally convergent and must be treated accordingly using the Ewald method.<sup>12,13</sup> To illustrate this necessity, we show in Fig. 1 the slow convergence of the Coulombic energy in a crystal of  $\alpha$ -quartz as a function of the cut-off radius of the truncation.

The aim of the present article is twofold. First, we show that the long-ranged many-body contribution due to the Ewald summation in reciprocal space can be treated analytically and be incorporated in the nonaffine response theory. Second, using  $\alpha$ -quartz as a

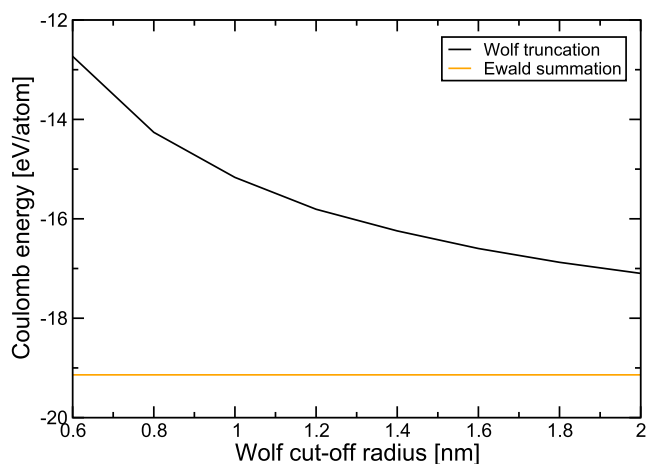

**FIG. 1.** Coulomb energy computed in a crystal of  $\alpha$ -quartz ( $a = 4.94 \text{ \AA}$ ,  $c = 5.44 \text{ \AA}$ ) with Wolf truncation as a function of the cut-off radius of the truncation. The horizontal line is the exact value, computed with Ewald summation. The Wolf-truncated energy decreases approximately as  $E_{\text{Ewald}} + 4/R_c$ , where  $E_{\text{Ewald}}$  is the value obtained with Ewald summation and  $R_c$  is the cut-off radius of the Wolf truncation.

prototypical noncentrosymmetric crystal, we show that, contrary to what might be expected, nonaffine contributions are not small corrections to the elastic constants: they are substantial (negative) contributions, which make the resulting elastic constants up to 4 times smaller than the affine estimates. This important fact has been overlooked in previous studies on  $\alpha$ -quartz lattice dynamics.<sup>14</sup>

These results are also relevant to studies of the boson peak [i.e., excess with respect to Debye's  $\omega^2$  law in the vibrational density of states (VDOS)], which is typically observed in glasses but has also recently been measured in organic crystals<sup>15–17</sup> as well as  $\alpha$ -quartz.<sup>18</sup> The boson peak in such crystals should be distinguished from a van Hove singularity as shown in Ref. 19. Recent works have highlighted the close connection between nonaffine elasticity and the boson peak anomaly,<sup>20,21</sup> and it has been suggested that the root cause of both boson peak and nonaffine elasticity could be traced back to the inherent lack of centrosymmetry of both glasses and noncentrosymmetric crystals such as  $\alpha$ -quartz.<sup>20</sup>

## II. ATOMISTIC SIMULATIONS OF $\alpha$ -QUARTZ CRYSTAL

### A. Lattice structure

X-ray and neutron crystallography have been applied to many materials to determine the crystal structure and atomic positions, including  $\alpha$ -quartz. It has been shown that crystals of  $\alpha$ -quartz have a trigonal Bravais lattice composed of  $\text{SiO}_4$  tetrahedra that are linked together at their corners to form a three-dimensional network.<sup>22</sup> The conventional unit cell, shown in Fig. 2, is hexagonal and contains three molecules of  $\text{SiO}_2$ . Its  $c$ -axis is a threefold screw axis; that is, the lattice remains unchanged after a rotation of  $120^\circ$  about this axis followed by a translation of  $+c/3$  along the same axis. Along the negative  $c$  direction, the screw axis is left-handed if the  $120^\circ$  rotation appears clockwise while if the rotation appears counterclockwise, the screw axis is right-handed.  $\alpha$ -quartz may exist in either of these forms, which are enantiomorphs (mirror images).  $\alpha$ -quartz crystals rotate the polarization of light propagating parallel to the  $c$ -axis, which is therefore also called the optical axis. Perpendicular to the  $c$ -axis are three twofold axes that are separated from one another by angles of  $120^\circ$  and intercept the  $c$ -axis at intervals of  $c/3$ . The absence of an inversion center allows  $\alpha$ -quartz to exhibit piezoelectricity when pressed along one of the twofold axes that are therefore often named electrical axes.<sup>22</sup>

Two space groups,  $P3_121$  or  $P3_221$ , can be used to label  $\alpha$ -quartz, depending on whether the  $c$ -axis is left- or right-handed. Before performing an energy minimization (see Sec. II C), we started with the lattice constants obtained experimentally from Bragg and Gibbs,<sup>23</sup> Wyckoff,<sup>24</sup> and Kihara,<sup>25</sup> with lattice parameters  $a$  and  $c$  at 298 K equal to 4.9137 and 5.4047  $\text{\AA}$ . The atomic positions of left-handed  $\alpha$ -quartz are given in the right-handed hexagonal coordinate systems in Table I.

### B. Empirical potential

In the present work, the cohesion of  $\alpha$ -quartz is modeled with the classical BKS potential, which is based on a short-range Buckingham potential and long-range Coulombic interactions

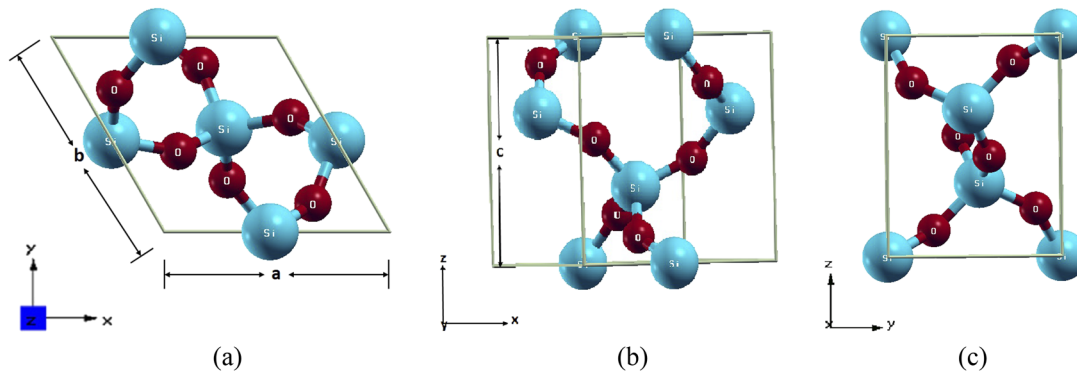


FIG. 2. Unit cell of  $\alpha$ -quartz from different perspectives: (a) top view, (b) left view, and (c) front view. Si atoms are in cyan and O atoms are in red.

between partial charges on Si and O atoms. Different parameterizations of this potential exist.<sup>26,27</sup> We have used the original parameters,<sup>26</sup> which do not include any direct Si-Si interaction, because they provide the best agreement with experimental measurements of elastic constants of  $\alpha$ -quartz.<sup>28</sup> The short-ranged potential between atoms  $i$  and  $j$  is expressed as

$$\Phi_{ij}^{sh}(R_{ij}) = \left\{ A_{ij} e^{-\frac{R_{ij}}{\rho_{ij}}} - \frac{C_{ij}}{R_{ij}^6} - \left[ A_{ij} e^{-\frac{R_{c,sh}}{\rho_{ij}}} - \frac{C_{ij}}{R_{c,sh}^6} \right] \right\} \Theta(R_{c,sh} - R_{ij}), \quad (1)$$

where  $\Theta$  is the Heaviside function and  $R_{ij}$  is the distance between atoms  $i$  and  $j$ . The parameters of the potential are given in Table II. The best agreement with experimental data is obtained for  $R_{c,sh} = 10 \text{ \AA}$ .<sup>28</sup>

In order to treat the Coulombic interactions analytically, we used the classical Ewald method.<sup>1,12,13,29</sup> In this approach, the point charge distribution, which is described by delta functions, is transformed by adding and subtracting Gaussian distributions. The total electrostatic energy is then rewritten as the sum of a short-range term ( $E_{SR}$ , difference between point- and Gaussian charge distributions) in real space, a long-range term ( $E_{LR}$ ,

Gaussian charge distribution) in Fourier space plus a self-interaction constant ( $E_{SI}$ ),

$$E \equiv E_{SR} + E_{LR} + E_{SI} \\ = \frac{1}{4\pi\epsilon_0} \frac{1}{2} \sum_{i \neq j} \frac{q_i q_j}{R_{ij}} \operatorname{erfc}\left(\frac{R_{ij}}{\sqrt{2}\sigma}\right) + \frac{1}{2V\epsilon_0} \sum_{\mathbf{G} \neq 0} \frac{\exp(-\sigma^2 G^2/2)}{G^2} |S(\mathbf{G})|^2 \\ - \frac{1}{4\pi\epsilon_0} \frac{1}{\sqrt{2\pi}\sigma} \sum_i q_i^2, \quad (2)$$

where  $q_i$  is the charge on atom  $i$ ,  $\operatorname{erfc}(z) = 1 - 2/\sqrt{\pi} \int_0^z \exp(t^2) dt$  is the complementary error function,  $\mathbf{G} = 2\pi[n_x/L_x, n_y/L_y, n_z/L_z]$  with  $(n_x, n_y, n_z) \in \mathbb{Z}^3$  refers to reciprocal lattice vectors, and  $S(\mathbf{G}) = \sum_j q_j \exp(i\mathbf{G} \cdot \mathbf{R}_j)$  is the structure factor. Here,  $\mathbf{R}_j$  is the position of atom  $j$  and  $R_{ij}$  is the distance between atoms  $i$  and  $j$ . In addition,  $L_x, L_y, L_z$  are the dimensions of the simulation cell, which is assumed periodic and orthogonal and of volume  $V = L_x L_y L_z$ . The parameter  $\sigma$  is the standard deviation of the Gaussian distribution. It sets the crossover between the real and reciprocal terms, which both converge absolutely and rapidly. Noting  $\alpha = 1/\sqrt{2}\sigma$ , we employed a cut-off radius for the real space potential  $R_{cut} = 3.2/\alpha$  and performed the summations in reciprocal space up to  $n_{\kappa,max} = \alpha L_{\kappa}$ . We used  $R_{cut} = 10 \text{ \AA}$ , which is a trade-off between the computing times of the short-ranged term,  $E_{SR}$ , and of the long-range summation in Fourier space,  $E_{LR}$ .

In the following, the short-range and self-interaction terms will be included in the short-range BKS term of Eq. (1). This term can be treated with the original approach of Lemaitre and Maloney,<sup>3</sup> which

TABLE I. Fractional coordinates of atoms of left-handed  $\alpha$ -quartz given in the scaled unit at 298 K at ambient pressure.<sup>25</sup>

Atom	x	y	z
Si	0.4697	0	0
Si	0	0.4697	2/3
Si	0.5303	0.5303	1/3
O	0.4133	0.2672	0.1188
O	0.2672	0.4133	0.5479
O	0.7328	0.1461	0.7855
O	0.5867	0.8539	0.2145
O	0.8539	0.5867	0.4521
O	0.1461	0.7328	0.8812

TABLE II. Parameters of the empirical potential used to model  $\alpha$ -quartz.

	$A_{ij}$ (eV)	$\rho_{ij}$ ( $\text{\AA}$ )	$C_{ij}$ (eV $\text{\AA}^6$ )
O-O	1 388.773	0.3623	175.0
Si-O	18 003.7572	0.2052	133.5381

is summarized in Sec. III A. Only  $E_{LR}$  requires a special treatment because of its many-body nature, as detailed in Sec. III B.

### C. Simulation procedure

Since we consider the properties of a perfect crystal, the system can in principle be limited to a single unit cell. In practice, we used a small but finite system, containing 1350 atoms in a periodic orthogonal cell. We started from the lattice positions in Table I and the experimental lattice constants.<sup>23–25</sup> We then relaxed the simulation cell at 0 K by energy minimization, adapting the cell dimensions with a barostat to impose zero internal stresses. The equilibrium lattice constants thus obtained are  $a = 4.94$  and  $c = 5.44$  Å, close to the values obtained experimentally<sup>30</sup> and by first-principles calculations.<sup>31</sup> The corresponding density,  $2.60$  g/cm<sup>3</sup>, is close to the experimental value of  $2.65$  g/cm<sup>3</sup>.<sup>32,33</sup>

To validate the analytical expressions of the elastic constants, we computed numerically their values by straining the crystal in small increments ( $10^{-5}$ ) and computing the slope of the resulting stress-strain curves. To obtain the affine constants, no relaxation was allowed between affine deformation steps, i.e., the atoms remained at their affine positions, while the nonaffine constants were computed by relaxing the atomic positions at fixed cell shape between each strain increment.

## III. NONAFFINE LATTICE DYNAMICS FORMALISM WITH THE EWALD METHOD

### A. Contribution of pairwise potential

We start by summarizing the expressions of the affine and nonaffine elastic constants in the case of particles that interact through a short-ranged pairwise potential,  $V_{ij}(r)$ . We consider a system of  $N$  atoms of mass  $\{M_i\}$  in a volume  $V$ . Defining  $t_{ij} = \frac{\partial V_{ij}}{\partial R_{ij}}$  and  $c_{ij} = \frac{\partial^2 V_{ij}}{\partial R_{ij}^2}$ , one can show<sup>3,5,7</sup> that the elastic constants are written as the difference between the affine (or Born) elastic constants and nonaffine terms,

$$C_{\alpha\beta\kappa\chi} = C_{\alpha\beta\kappa\chi}^{\text{Born}} - \frac{1}{V} \sum_{m=1}^{3N-3} \frac{C_{m,\alpha\beta} C_{m,\kappa\chi}}{\omega_m^2}. \quad (3)$$

The affine elastic constants are expressed as

$$\begin{aligned} C_{\alpha\beta\kappa\chi}^{\text{Born}} &= -\frac{1}{4V} \sum_{i \neq j} [D_{ij}^{\alpha\kappa} R_{ij}^\beta + D_{ij}^{\beta\kappa} R_{ij}^\alpha] R_{ij}^\chi \\ &= \frac{1}{2V} \sum_{i \neq j} (R_{ij} c_{ij} - t_{ij}) R_{ij} n_{ij}^\alpha n_{ij}^\beta n_{ij}^\kappa n_{ij}^\chi, \end{aligned} \quad (4)$$

where  $D_{ij}^{\alpha\beta}$  is the dynamical matrix of the system,  $\mathbf{R}_{ij}$  is the vector between atoms  $i$  and  $j$ , and  $\mathbf{n}_{ij}$  is the corresponding unit vector. The nonaffine term is written as a sum over the normal modes  $m$  of the system with  $C_m$ , a mode-dependent tensor expressed as

$$C_{m,\kappa\chi} = -\sum_{j\alpha} \Xi_{j,\kappa\chi}^\alpha \frac{e_j^\alpha(m)}{\sqrt{M_j}}, \quad (5)$$

where  $e_j^\alpha(m)$  is the component on atom  $j$  and direction  $\alpha$  of the  $m$ th eigenvector of the mass-scaled dynamical matrix of the system. The corresponding eigenfrequency,  $\omega_m$ , appears in Eq. (3).  $\Xi_{j,\kappa\chi}^\alpha$  is

the nonaffine force vector field, which corresponds to the force that appears on the atoms when an incremental affine deformation  $d\epsilon_{\kappa\chi}$  is applied to the system. This force drives nonaffine relaxations. For a pair potential, we have the following equation:

$$\begin{aligned} \Xi_{i,\kappa\chi}^\alpha &= \frac{\partial F_i^\alpha}{\partial \epsilon_{\kappa\chi}} = -\frac{1}{2} \sum_j (D_{ij}^{\alpha\kappa} R_{ij}^\beta + D_{ij}^{\alpha\beta} R_{ij}^\kappa) \\ &= -\sum_j (R_{ij} c_{ij} - t_{ij}) n_{ij}^\alpha n_{ij}^\kappa n_{ij}^\chi. \end{aligned} \quad (6)$$

### B. Ewald sum contribution

We now consider the contribution of the long-ranged term  $E_{LR}$  in Eq. (2) to the affine and nonaffine elastic constants. The expressions in Eqs. (3) and (5) remain valid, but we need to express the contribution of  $E_{LR}$  to the dynamical matrix, the affine elastic constants, and the nonaffine forces.

#### 1. Forces and dynamical matrix

The long-ranged energy  $E_{LR}$  produces atomic forces due to the dependence of the structure factor,  $S(\mathbf{G}) = \sum_j q_j \exp(i\mathbf{G} \cdot \mathbf{R}_j)$ , on atomic positions. The expression of the resulting force is as follows:<sup>13,29</sup>

$$\begin{aligned} \mathbf{F}_i &= -\frac{\partial E_{LR}}{\partial \mathbf{R}_i} \\ &= -\frac{1}{2V\epsilon_0} \sum_{\mathbf{G} \neq 0} \frac{\exp(-\sigma^2 G^2/2)}{G^2} [S(\mathbf{G})(-i\mathbf{G}) q_i e^{-i\mathbf{G} \cdot \mathbf{R}_i} \\ &\quad + S(-\mathbf{G}) q_i (i\mathbf{G}) e^{i\mathbf{G} \cdot \mathbf{R}_i}] \\ &= -\frac{1}{V\epsilon_0} \sum_{\mathbf{G} \neq 0} \frac{\exp(-\sigma^2 G^2/2)}{G^2} \mathbf{G} q_i \text{Im}[S(\mathbf{G}) e^{-i\mathbf{G} \cdot \mathbf{R}_i}] \\ &= \frac{q_i}{V\epsilon_0} \sum_{\mathbf{G} \neq 0} \frac{\exp(-\sigma^2 G^2/2)}{G^2} \mathbf{G} \sum_j q_j \sin(\mathbf{G} \cdot \mathbf{R}_{ij}). \end{aligned} \quad (7)$$

In the following, we simplify the notations by noting  $I(u) = \exp(-\sigma^2 u/2)/u$ , such that the contribution of the Ewald long-range term to the atomic force is written as

$$\mathbf{F}_i = \frac{q_i}{V\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) \mathbf{G} \sum_j q_j \sin(\mathbf{G} \cdot \mathbf{R}_{ij}). \quad (8)$$

The long-range contribution to dynamical matrix elements can be computed likewise:

1.  $i \neq j$ :

$$D_{ij}^{\alpha\beta} = \frac{\partial^2 E_{LR}}{\partial R_i^\alpha \partial R_j^\beta} = \frac{q_i q_j}{V\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) G^\alpha G^\beta \cos(\mathbf{G} \cdot \mathbf{R}_{ij}). \quad (9)$$

2.  $i = j$ :

$$D_{ii}^{\alpha\beta} = -\frac{q_i}{V\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) G^\alpha G^\beta \sum_{j \neq i} q_j \cos(\mathbf{G} \cdot \mathbf{R}_{ij}) = -\sum_{j \neq i} D_{ij}^{\alpha\beta}.$$

#### 2. Tensile deformation

To find the long-range effect on the nonaffine forces, we need to express the variation of the atomic force in Eq. (8) when an incremental affine strain is applied to the system. We consider first a

uniaxial strain  $\epsilon$  along direction  $x$ . The dependence on  $\epsilon$  is due to the dependence of three terms:

- the volume,  $V \rightarrow V(1 + \epsilon)$ ;
- the reciprocal vectors, which in an orthogonal box become  $\mathbf{G} \rightarrow 2\pi\{n_x/L_x(1 + \epsilon), n_y/L_y, n_z/L_z\}$ ; and
- the atom-to-atom vectors,  $\mathbf{R}_{ij} \rightarrow [R_{ij}^x(1 + \epsilon), R_{ij}^y, R_{ij}^z]$ .

We note that with these transformations,  $\mathbf{G} \cdot \mathbf{R}_{ij}$  is unchanged and so that the structure factor  $S(\mathbf{G})$  is constant. Taking the derivative of  $\mathbf{F}_i$  in Eq. (8) with respect to  $\epsilon$ , we obtain in the limit  $\epsilon \rightarrow 0$ ,

$$\Xi_{i,xx} = -\frac{q_i}{V\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) \left( \sigma^2 + \frac{2}{G^2} \right) G_x^2 \mathbf{G} \sum_j q_j \sin(\mathbf{G} \cdot \mathbf{R}_{ij}). \quad (10)$$

Taking the first and second derivatives of  $E_{LR}$  with respect to  $\epsilon$ , we obtain the tensile stress and affine elastic constants for the tensile strain,

$$\begin{aligned} \sigma_{xx} &= \lim_{\epsilon \rightarrow 0} \frac{1}{V} \frac{\partial E_{LR}}{\partial \epsilon} \\ &= \frac{1}{2V^2\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) |S(\mathbf{G})|^2 \left( \left[ \sigma^2 + \frac{2}{G^2} \right] G_x^2 - 1 \right) \end{aligned} \quad (11)$$

and

$$\begin{aligned} C_{xxxx}^{Born} &= \lim_{\epsilon \rightarrow 0} \frac{1}{V} \frac{\partial^2 E_{LR}}{\partial \epsilon^2} \\ &= \frac{1}{V^2\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) |S(\mathbf{G})|^2 \left( 1 - \frac{5}{2} \left[ \sigma^2 + \frac{2}{G^2} \right] G_x^2 \right. \\ &\quad \left. + \left[ \frac{4}{G^4} + 2 \frac{\sigma^2}{G^2} + \frac{\sigma^4}{2} \right] G_x^4 \right). \end{aligned} \quad (12)$$

Similar expressions are obtained for tensile deformations along  $y$  and  $z$ . Finally, the cross-terms are expressed as

$$\begin{aligned} C_{\alpha\alpha\kappa\kappa}^{Born} &= \frac{1}{V^2\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) |S(\mathbf{G})|^2 \left( \frac{1}{2} - \left[ \sigma^2 + \frac{2}{G^2} \right] \right. \\ &\quad \left. \times \frac{G_\alpha^2 + G_\kappa^2}{2} + \left[ \frac{4}{G^4} + 2 \frac{\sigma^2}{G^2} + \frac{\sigma^4}{2} \right] G_\alpha^2 G_\kappa^2 \right) \end{aligned} \quad (13)$$

for Cartesian components  $\alpha, \kappa$ .

### 3. Shear deformation

We now consider the case of an affine shear strain parallel to the  $y$  planes with displacements along the  $x$  direction. The applied strain is noted  $\gamma_{xy} \equiv \gamma$ . Under this strain, the axis of the box becomes  $\mathbf{a}'_1 = (L_x, 0, 0) = \mathbf{a}_1$ ,  $\mathbf{a}'_2 = (L_x\gamma, L_y, 0)$ ,  $\mathbf{a}'_3 = (0, 0, L_z) = \mathbf{a}_3$  while the reciprocal vectors become  $\mathbf{G}' = 2\pi\left(\frac{n_x}{L_x}, \frac{n_y}{L_y} - \frac{n_x\gamma}{L_x}, \frac{n_z}{L_z}\right)$  and the atom-to-atom vectors become  $\mathbf{R}'_{ij} = (R_{ij}^x + R_{ij}^y\gamma, R_{ij}^y, R_{ij}^z)$ . One can check that again  $\mathbf{G} \cdot \mathbf{R}_{ij}$  is unchanged during the transformation. After taking the derivative of the long-range force in Eq. (8) with respect to  $\gamma$ , we obtain in the limit  $\gamma \rightarrow 0$ ,

$$\Xi_{i,xy} = -\frac{q_i}{V\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) \left( \sigma^2 + \frac{2}{G^2} \right) G_x G_y \mathbf{G} \sum_j q_j \sin(\mathbf{G} \cdot \mathbf{R}_{ij}). \quad (14)$$

Similarly, the shear stress is expressed as

$$\sigma_{xy} = \frac{1}{2V^2\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) |S(\mathbf{G})|^2 \left( \sigma^2 + \frac{2}{G^2} \right) G_x G_y \quad (15)$$

and the affine elastic constant as

$$\begin{aligned} C_{xyxy}^{Born} &= \lim_{\gamma \rightarrow 0} \frac{\partial \sigma_{xy}}{\partial \gamma} = \frac{1}{2V^2\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) |S(\mathbf{G})|^2 \\ &\quad \times \left( \sigma^4 + 4 \frac{\sigma^2}{G^2} + \frac{8}{G^4} \right) G_x^2 G_y^2. \end{aligned} \quad (16)$$

### 4. Some other affine elastic constants from $E_{LR}$

We note that the formula of Born approximation hold for a generic strain tensor  $\underline{\eta}$ ,

$$C_{\alpha\beta\kappa\lambda}^{Born} = \lim_{\underline{\eta} \rightarrow 0} \frac{1}{V} \frac{\partial E_{LR}}{\partial \eta_{\alpha\beta} \partial \eta_{\kappa\lambda}}. \quad (17)$$

For  $C_{16} = C_{xxxy}$ ,  $C_{14} = C_{xxyy}$  and  $C_{56} = C_{xyyz}$ , we have, respectively,

$$\begin{aligned} C_{xxxy} &= \frac{1}{2V^2\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) |S(\mathbf{G})|^2 \left[ \left( \sigma^4 + \frac{4\sigma^2}{G^2} + \frac{4}{G^4} \right) G_x^2 - \left( \sigma^2 + \frac{2}{G^2} \right) \right. \\ &\quad \left. \times G_x G_y + \frac{1}{2V^2\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) |S(G^2)|^2 \frac{2G_x^2}{G^4} 2G_x G_y \right. \\ &= \frac{1}{2V^2\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) |S(G^2)|^2 \\ &\quad \left. \times \left[ \left( \sigma^4 + \frac{4\sigma^2}{G^2} + \frac{8}{G^4} \right) G_x^2 - \sigma^2 - \frac{2}{G^2} \right] G_x G_y, \end{aligned} \quad (18)$$

$$\begin{aligned} C_{xxyy} &= \frac{1}{2V^2\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) |S(G^2)|^2 \\ &\quad \times \left[ \left( \sigma^4 + \frac{4\sigma^2}{G^2} + \frac{8}{G^4} \right) G_x^2 - \sigma^2 - \frac{2}{G^2} \right] G_y G_z, \end{aligned} \quad (19)$$


$$\begin{aligned} C_{xyyz} &= \frac{1}{2V^2\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) |S(G^2)|^2 \left( \sigma^4 + \frac{4\sigma^2}{G^2} + \frac{4\sigma^2}{G^2} \right) G_x G_y G_x G_z \\ &\quad + \frac{1}{2V^2\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) |S(G^2)|^2 \frac{4}{G^4} G_x G_y G_x G_z \\ &= \frac{1}{2V^2\epsilon_0} \sum_{\mathbf{G} \neq 0} I(G^2) |S(G^2)|^2 \left( \sigma^4 + \frac{8\sigma^2}{G^2} + \frac{4\sigma^2}{G^2} \right) G_x G_y G_x G_z. \end{aligned} \quad (20)$$

## IV. RESULTS AND DISCUSSION

We first use Eq. (9) to compute the dynamical matrix of the present atomic-scale model of  $\alpha$ -quartz and, after diagonalization,

obtain the vibrational density of states (VDOS). The result is shown in Fig. 3(a), with a comparison to the experimental data obtained by Chumakov *et al.*<sup>18</sup> The present implementation of the BKS model predicts accurately the first peak of the VDOS, which occurs at about 10 meV. The second peak is reproduced only qualitatively, being located at a slightly higher frequency (18 instead of 16 meV) and with a slightly lower amplitude. Normalizing the VDOS by  $\omega^2$  in Fig. 3(b), we see that the numerical model reproduces well the boson peak reported experimentally. We can conclude that the present model reproduces satisfactorily the VDOS and boson peak of  $\alpha$ -quartz.

Second, we use Eq. (3) with the short- and long-ranged terms presented above to compute both the affine and total elastic constants of  $\alpha$ -quartz. The result is given in Table III with a comparison to experimental data. We checked by direct numerical calculations that the analytical expressions described in Sec. III predict

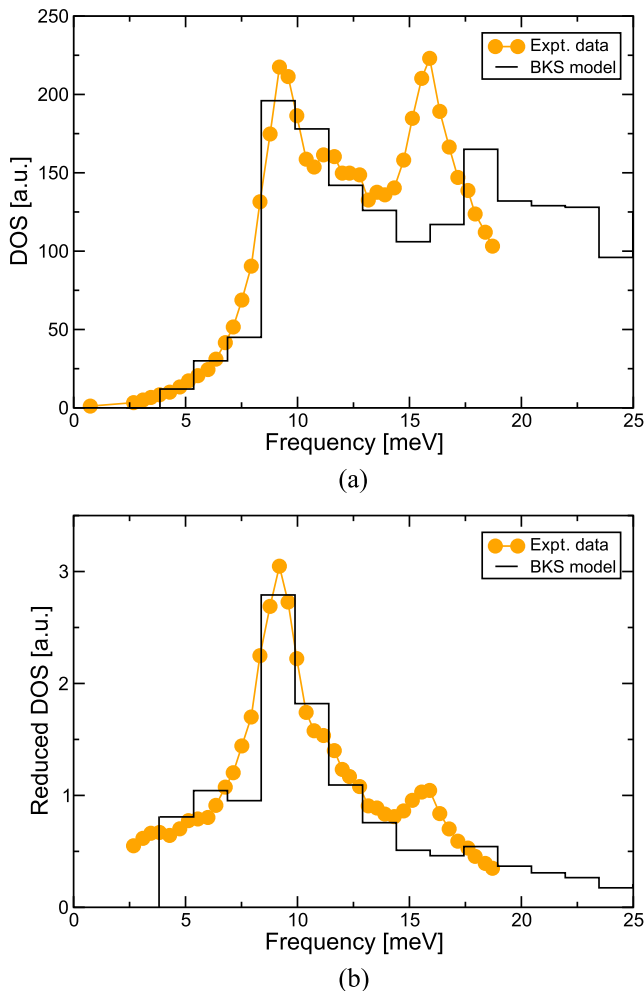

**FIG. 3.** Comparison of the density of states and (a) reduced density of states (DOS normalized by the frequency squared) (b) obtained numerically with the BKS model and experimentally with inelastic x-ray scattering.<sup>18</sup>

**TABLE III.** Comparison between experimental measurements of the elastic constants of  $\alpha$ -quartz and the present numerical calculations, including both affine and nonaffine contributions or only the affine part.

Elast. Const. (GPa)	$C_{11}$	$C_{33}$	$C_{44}$	$C_{66}$	$C_{12}$	$C_{13}$
Affine+Nonaffine	90.5	107.0	50.2	41.1	8.1	15.2
Affine only	375.6	329.6	189.2	125.4	125.2	189.1
Expt. <sup>34</sup>	86.8	105.8	58.2	39.9	7.0	19.1
Expt. <sup>32</sup>	87.3	105.8	57.2	40.4	6.57	12.0
Expt. <sup>33</sup>	86.6	106.4	58		6.74	12.4

faithfully the elastic constants. We chose the same parameterization of the BKS potential and Ewald summation as Carré *et al.*<sup>28</sup> because they yield a very good agreement with experimental data, as seen in Table III, when both the affine and nonaffine contributions are included. On the other hand, when only the affine deformation is allowed, the elastic constants are largely overestimated, by a factor 3–4 for  $C_{11}$ ,  $C_{33}$ ,  $C_{44}$ ,  $C_{66}$ , and up to a factor of 15 for  $C_{12}$  and  $C_{13}$ . In other words, the nonaffine correction decreases the affine elastic constants by about 70% for  $C_{11}$ ,  $C_{33}$ ,  $C_{44}$ ,  $C_{66}$ , and up to 90% for  $C_{12}$  and  $C_{13}$ .

By way of comparison, if we use a more recent parameterization of BKS potential,<sup>27</sup> which includes direct interactions between Si atoms, the equilibrium density is lower, 2.42 g/cm<sup>3</sup>, and the elastic constants are further from the experimental data ( $C_{11} = 100.7$  GPa,  $C_{33} = 79.4$  GPa,  $C_{44} = 41.8$  GPa,  $C_{66} = 56.8$  GPa,  $C_{12} = -12.6$  GPa,  $C_{13} = 2.9$  GPa). However, the effect of the nonaffine relaxations remains of the same order as with the parameterization of BKS potential used above.

The nonaffine relaxations originate from the lack of symmetry of the  $\alpha$ -quartz crystal.<sup>7,20</sup> This is evident for the short-ranged pair potential part of the interatomic potential since in Eq. (6), the nonaffine force vector,  $\Xi_i$ , which drives the nonaffine relaxations, is written as a sum over neighbors of terms of the type  $D_{ij}^{\alpha\beta} R_{ij}^{\kappa}$  that add up to zero in a centrosymmetric environment. The same is true for the long-range terms in Eqs. (10) and (14), which depend on  $\sum_j q_j \sin(\mathbf{G} \cdot \mathbf{R}_{ij})$ , which is also zero if atom  $i$  is a center of centrosymmetry. In  $\alpha$ -quartz, neither Si nor O atoms are centers of symmetry, which may explain why nonaffine relaxations are so important in this crystal. However, Si atoms are surrounded by close-to-perfect tetrahedra of O atoms as explained in Sec. II A, while O atoms are in clearly asymmetrical environments since the Si–O–Si bonds are not straight, but make an angle close to 148°. The higher symmetry of the environment of the Si atoms implies more limited nonaffine relaxations for these atoms. The latter depend on the imposed deformation, but we have checked that the nonaffine displacements of the Si atoms is systematically at least a factor of 2 smaller than that of the O atoms.

It was suggested in a recent work<sup>20</sup> that the lack of centrosymmetry is responsible not only for the nonaffinity of the elastic constants, but also for the boson peak that shows up in the VDOS of glasses and noncentrosymmetric crystals. In the work by Milkus and Zaccane,<sup>20</sup> model systems were studied numerically, which included random spring networks derived from glasses and crystals with random bond-depletion. A universal correlation was found between the boson peak amplitude and a new order parameter for

centrosymmetry (but importantly, *not* with the standard bond-orientational order parameter), which allowed for the collapse of data from systems with very different lattice topologies (i.e., random networks and defective crystals).

The present findings demonstrate that strong nonaffine elasticity originates from noncentrosymmetry of the lattice also in *perfectly ordered* (defect-free) noncentrosymmetric crystals such as  $\alpha$ -quartz. Also in this case, the strong nonaffinity of the elastic constants is accompanied by a pronounced boson peak in the normalized VDOS, which shows up in both experimental measurements and atomic-scale simulations, in perfect mutual agreement as shown in Fig. 3.

These observations raise the fundamental question about the microscopic mechanism, which links the atomic-scale noncentrosymmetry of the lattice and the boson peak in the VDOS. In all systems studied so far, including the defective crystals of Refs. 20, the boson peak frequency is very close to the frequency of the Ioffe-Regel crossover at which the phonons wavelength becomes smaller than their mean-free path and the phonons become quasilocalized. In glasses, this phenomenon is obviously driven by disorder, which is responsible for the scattering of the phonons on sufficiently small wavelengths. In a system such as  $\alpha$ -quartz, it remains to be established whether noncentrosymmetry alone can induce similar scattering processes, which would lead to the peak. To elucidate this point, it will be necessary, in future work, to study more in detail the microscopic mechanism of the phonon propagation and how this is affected by noncentrosymmetry. For example, the noncentrosymmetry of the lattice has been recently shown to generate new physics in the phonon propagation, including chiral phonons.<sup>35</sup>

## V. CONCLUSION

We have shown in the paper that employing an empirical potential for  $\alpha$ -quartz, with long-range Coulombic effects explicitly considered, the elastic constants of  $\alpha$ -quartz, consisting of the contribution of affine and nonaffine contributions, can be excellently recovered. It was found that the nonaffine force field in a noncentrosymmetric lattice plays a crucial role in the elastic constants. This is the first time that strong nonaffine elasticity, which is a defining property of glasses, is quantitatively revealed in a perfectly crystalline material without defects. This result therefore hints at the possibility that glassy anomalies (including the boson peak) might be more general than accepted so far. Moreover, we considered here static elastic constants, but the present framework can be readily extended to consider lattice dynamics at finite frequencies.<sup>7</sup> Furthermore, the dynamical structure factor can also be easily calculated and comparison with experimental data will be a subject of a future study. Finally, the vibrational spectrum calculated here is important to predict dielectric constant and infrared optical properties of the material, also in an effort to understand the divergence of the dielectric constant at the  $\alpha$ - $\beta$  transition of quartz.<sup>36</sup>

## ACKNOWLEDGMENTS

B.C. acknowledges the financial support from CSC-Cambridge Scholarship. D.R. acknowledges support from LABEX iMUST (Grant No. ANR-10-LABX-0064) of Université de Lyon (programme Investissements d'Avenir, Grant No. ANR-11-IDEX-0007).

## REFERENCES

- 1 M. Born and K. Huang, *Dynamical Theory of Crystal Lattices* (Oxford University Press, Oxford, 1954).
- 2 B. Holm and R. Ahuja, "Ab initio calculation of elastic constants in SiO<sub>2</sub> stishovite and  $\alpha$ -quartz," *J. Chem. Phys.* **111**, 2071 (1999).
- 3 A. Lemaitre and C. Maloney, "Sum rules for the quasi-static and visco-elastic response of disordered solids at zero temperature," *J. Stat. Phys.* **123**, 415 (2006).
- 4 J. F. Lutsko, "Generalized expressions for the calculation of elastic constants by computer simulations," *J. Appl. Phys.* **65**, 2991 (1989).
- 5 A. Zaccone and E. Scossa-Romano, "Approximate analytical description of the nonaffine response of amorphous solids," *Phys. Rev. B* **83**, 184205 (2011).
- 6 A. Zaccone and E. M. Terentjev, "Disorder-assisted melting and the glass transition in amorphous solids," *Phys. Rev. Lett.* **110**, 178002 (2013).
- 7 T. Damart, A. Tanguy, and D. Rodney, "Theory of harmonic dissipation in disordered solids," *Phys. Rev. B* **95**, 054203 (2017).
- 8 V. V. Palyulin, C. Ness, R. Milkus, R. M. Elder, T. W. Sirk, and A. Zaccone, "Parameter-free predictions of the viscoelastic response of glassy polymers from nonaffine lattice dynamics," *Soft Matter* **14**, 8475 (2018).
- 9 D. Wolf, P. Kéblinski, S. R. Phillpot, and J. Eggebrecht, "Exact method for the simulation of coulombic systems by spherically truncated, pairwise r-1 summation," *J. Chem. Phys.* **110**, 8254 (1999).
- 10 C. J. Fennell and J. D. Gezelter, "Is the Ewald summation still necessary? Pairwise alternatives to the accepted standard for long-range electrostatics," *J. Chem. Phys.* **124**, 234104 (2006).
- 11 A. Carré, L. Berthier, J. Horbach, S. Ispas, and W. Kob, "Amorphous silica modeled with truncated and screened coulomb interactions: A molecular dynamics simulation study," *J. Chem. Phys.* **127**, 114512 (2007).
- 12 P. P. Ewald, "The calculation of optical and electrostatic grid potential," *Ann. Phys. (Leipzig)* **64**, 253 (1921).
- 13 H. Lee and W. Cai, "Ewald summation for Coulomb interactions in a periodic supercell," Lecture Notes (Stanford University, 2009).
- 14 A. Bosak *et al.*, "New insights into the lattice dynamics of  $\alpha$ -quartz," *Z. Kristallogr.* **227**, 84 (2012).
- 15 J. F. Gebbia, M. A. Ramos, D. Szweczyk, A. Jerowski, A. I. Krivchikov, Y. V. Horbatenko, T. Guidi, F. J. Bermejo, and J. L. Tamarit, "Glassy anomalies in the low-temperature thermal properties of a minimally disordered crystalline solid," *Phys. Rev. Lett.* **119**, 215506 (2017).
- 16 A. Jeżowski, M. A. Strzemechny, A. I. Krivchikov, N. A. Davydova, D. Szweczyk, S. G. Stepanian, L. M. Buravtseva, and O. O. Romantsova, "Glassy anomalies in the heat capacity of an ordered 2-bromobenzophenone single crystal," *Phys. Rev. B*, 201201(R) (2018).
- 17 M. Moratalla, J. F. Gebbia, M. A. Ramos, L. C. Pardo, S. Mukhopadhyay, S. Rudic, F. Fernandez-Alonso, F. J. Bermejo, and J. L. Tamarit, "Emergence of glassy features in halomethane crystals," *Phys. Rev. B* **99**, 024301 (2019).
- 18 V. I. Chumakov *et al.*, "Role of disorder in the thermodynamics and atomic dynamics of glasses," *Phys. Rev. Lett.* **112**, 025502 (2014).
- 19 Y. Wang, L. Hong, Y. Wang, W. Schirmacher, and J. Zhang, "Disentangling boson peaks and Van Hove singularities in a model glass," *Phys. Rev. B* **98**, 174207 (2018).
- 20 R. Milkus and A. Zaccone, "Local inversion-symmetry breaking controls the boson peak in glasses and crystals," *Phys. Rev. B* **93**, 094204 (2016).
- 21 S. Senguly and S. Sengupta, "Excess vibrational modes of a crystal in an external non-affine field," *J. Chem. Sci.* **129**, 891 (2017).
- 22 J. P. Sutter and H. Yavas, "Material properties of  $\alpha$ -quartz that are relevant for its potential use in X-ray monochromators and analyzers," e-print [arXiv:1612.07049](https://arxiv.org/abs/1612.07049) (2017).
- 23 W. Bragg and R. E. Gibbs, "The structure of  $\alpha$  and  $\beta$  quartz," *Proc. R. Soc. London, Ser. A* **109**, 405 (1925).
- 24 R. W. G. Wyckoff, *Crystal Structures* (John Wiley & Sons, New York, 1963), Vol. 1.



- <sup>25</sup>K. Kihara, "An X-ray study of the temperature dependence of the quartz structure," *Eur. J. Mineral.* **2**, 63 (1990).
- <sup>26</sup>B. W. H. van Beest, G. J. Kramer, and R. A. van Santen, "Force fields for silicas and aluminophosphates based on *ab initio* calculations," *Phys. Rev. Lett.* **64**, 1955 (1990).
- <sup>27</sup>B. Mantsi, A. Tanguy, G. Kermouche, and E. Barthel, "Atomistic response of a model silica glass under shear and pressure," *Eur. Phys. J. B* **85**, 304 (2012).
- <sup>28</sup>A. Carré, J. Horbach, S. Ispas, and W. Kob, "New fitting scheme to obtain effective potential from car-parrinello molecular-dynamics simulations: Application to silica," *Europhys. Lett.* **82**, 17001 (2008).
- <sup>29</sup>A. Y. Toukmaji and J. A. Board, "Ewald summation techniques in perspective: A survey," *Comput. Phys. Commun.* **95**, 73 (1996).
- <sup>30</sup>S. M. Antao, I. Hassan, J. Wang, P. L. Lee, and B. H. Toby, "State-of-the-art high-resolution powder x-ray diffraction (HRPXRD) illustrated with Rietveld structure refinement of quartz, sodalite, tremolite, and meionite," *Can. Mineral.* **46**, 1501–1509 (2008).
- <sup>31</sup>K. Mizokami, A. Togo, and I. Tanaka, "Lattice thermal conductivities of two SiO<sub>2</sub> polymorphs by first-principles calculations and the phonon Boltzmann transport equation," *Phys. Rev. B* **97**, 224306 (2018).
- <sup>32</sup>P. Heyliger, H. Ledbetter, and S. Kim, "Elastic constants of natural quartz," *J. Acoust. Soc. Am.* **114**, 644 (2003).
- <sup>33</sup>J. Wang, Z. Mao, F. Jiang, and T. S. Duffy, "Elasticity of single-crystal quartz to 10 GPa," *Phys. Chem. Miner.* **42**, 203 (2015).
- <sup>34</sup>G. Will, M. Bellotto, W. Parrish, and M. Hart, "Crystal structures of quartz and magnesium germanate by profile analysis of synchrotron-radiation high resolution power data," *J. Appl. Crystallogr.* **21**, 182 (1988).
- <sup>35</sup>H. Zhu, J. Yi, M.-Y. Li, J. Xiao, L. Zhang, C.-W. Yang, R. A. Kaindl, L.-J. Li, Y. Wang, and X. Zhang, "Observation of chiral phonons," *Science* **359**(6375), 579–582 (2018).
- <sup>36</sup>F. Gangemi, R. Gangemi, A. Carati, A. Maiocchi, and L. Galgani, "Infrared optical properties of  $\alpha$ -quartz by molecular dynamics simulations," *EPL* **116**, 37001 (2016).